



# EPS White Book

## EUMEPS Background Information on standardisation of EPS

Issued by EUMEPS in 2014  
Copyright EUMEPS 2014

Version 15/10/14

### Disclaimer

*The internet site [www.eumeps.org](http://www.eumeps.org) is property of EUMEPS in Belgium, registered under no. BE 453.127.976. The White Book is a part of the internet site. By visiting this site you agree that all matters between EUMEPS and yourself are governed by Belgian law. Any dispute in connection with this site shall be under the sole jurisdiction of the Brussels Court, excluding any other court.*

*The White Book: though EUMEPS tries to provide correct information from sources that are believed reliable, EUMEPS explicitly or implicitly does not offer any guarantee that the information given is correct, complete or actual. The information contained herein is subject to change. EUMEPS reserves the right to amend the information in this publication without notice. The information is provided for informational purposes only within EUMEPS. Decisions based on this information are your own responsibility and risk. EUMEPS is holder of the copyrights and all other rights with regard to the EUMEPS White Book which therefore may not be reproduced or transmitted without prior express consent by EUMEPS.*

## Content

<b>1</b>	<b>General .....</b>	<b>5</b>
1.1	Purpose and scope of this document .....	5
1.2	New approach of EPS in the market.....	5
1.3	Background .....	5
<b>2</b>	<b>Explanation of the structure of EPS Standards .....</b>	<b>9</b>
2.1	Introduction .....	9
2.2	Foreword.....	9
2.3	Scope .....	9
2.4	Normative references .....	10
2.5	Terms, definitions, symbols, units and abbreviated terms .....	10
2.5.1	Terms and definitions .....	10
2.5.2	Symbols, units and abbreviated terms .....	10
2.6	Requirements.....	10
2.7	Test methods .....	11
2.7.1	Sampling .....	11
2.7.2	Conditioning .....	11
2.7.3	Testing .....	11
2.8	Designation code .....	12
2.9	Evaluation of conformity .....	12
2.10	Marking and labelling .....	12
2.11	Annexes .....	13
2.11.1	Annex: Determination of the declared values of thermal resistance and thermal conductivity .....	13
2.11.2	Annex: Initial type testing (ITT) and factory production control (FPC).....	13
2.11.3	Annex: Product classification.....	14
2.11.4	Annex: Multi layered EPS products .....	14
2.11.5	Annex: Verification of the reaction to fire classification of raw materials .....	14
2.11.6	Annex: Additional properties (informative).....	14
2.11.7	Annex ZA: Clauses of this European standard addressing the provisions of the EU Construction Products Directive .....	14
2.12	Bibliography .....	18
2.13	In situ standards.....	18
2.13.1	EN 16025-1 .....	18
2.13.2	EN 16025-1 .....	18
2.13.3	EN 15037-4: 2010 + A1:2013, .....	19
2.13.4	EN 15037-5: 2013,.....	19
<b>3</b>	<b>Determination of characteristics .....</b>	<b>20</b>
3.1	Thermal resistance and thermal conductivity .....	20
3.2	Tolerances on Length and Width, Thickness, Squareness and Flatness .....	23
3.3	Reaction to fire.....	23
3.3.1	Reaction to fire classification of EPS products according to the CPR and the harmonised European standards.....	23
3.3.2	Behaviour of EPS in the presence of heat and different ignition sources .....	26
3.4	Durability .....	26
3.4.1	Durability of reaction to fire against heat, weathering, ageing/degradation.....	26
3.4.2	Durability of thermal resistance against heat, weathering, ageing/degradation .....	27
3.4.3	Durability of compressive strength against ageing and degradation .....	27
3.5	Dimensional stability .....	27
3.6	Compressive stress at 10% deformation.....	27
3.7	Bending strength.....	28
3.8	Tensile strength perpendicular to faces.....	29
3.9	Deformation under specific compressive load an temperature conditions .....	30
3.10	Compressive creep .....	31
3.11	Shear behaviour.....	34
3.12	Behaviour under cyclic loading .....	35
3.13	Compressive stress at 2 % and/or 5 % deformation .....	36
3.14	Product properties of EPS and Eurocodes .....	36
3.14.1	Short-term compressive strength.....	36

3.14.2	Creep and relaxation .....	38
3.14.3	Long term compressive strength .....	39
3.14.4	Modulus of elasticity.....	39
3.14.5	Compressive strength under cyclic load .....	39
3.15	Mechanical resistance and stability of the system.....	40
3.16	Tensile strength of the reinforcement .....	40
3.17	Resistance to impact .....	40
3.18	Resistance to penetration .....	40
3.19	Durability and adhesion of the finishing material on the base coat .....	40
3.20	Conditioning of the test specimen in accordance with EN 1062-11 .....	41
3.21	Water absorption.....	41
3.22	Long term water absorption by immersion .....	43
3.23	Long term water absorption by diffusion.....	43
3.24	Freeze thaw resistance.....	43
3.25	Water vapour transmission .....	44
3.26	Water vapour diffusion resistance factor .....	45
3.27	Liquid water permeability of the system surface.....	48
3.28	Characteristics for floating floors are listed in 3.27 and 3.28.....	48
3.29	Dynamic stiffness.....	48
3.30	Compressibility.....	51
3.31	Apparent density .....	51
3.32	Release of dangerous substances .....	51
3.32.1	General .....	51
3.32.2	Specific to EPS .....	52
3.33	Continuous glowing combustion .....	52
3.34	Maximum service temperature .....	52
3.35	Minimum service temperature .....	52
3.36	Trace quantities of water soluble ions and pH.....	53
3.37	Correlation between bending and tensile strength .....	53
3.38	Moisture content .....	53
3.39	Thermal expansion .....	53
3.40	Hygic expansion coefficient.....	55
3.41	Specific heat capacity .....	55
3.42	Chemical resistance.....	55
3.43	Air permeability .....	57
3.44	Electrical properties .....	57
3.45	Sustainability, LCA data and EPD's.....	57
<b>4</b>	<b>Application and calculation .....</b>	<b>58</b>
4.1	Eurocodes calculation rules for EPS .....	58
4.1.1	Introduction .....	58
4.1.2	Design rules .....	58
4.1.3	Loadings .....	58
4.1.4	Loading factors .....	58
<b>5</b>	<b>Design criteria .....</b>	<b>59</b>
5.1	International Application standards.....	61
5.2	European Calculation standards.....	61
5.3	National Application rules .....	62
5.4	European EPS Types .....	64
5.4.1	EUMEPS EPS types.....	64
5.4.2	Application .....	65
<b>6</b>	<b>Voluntary quality marks .....</b>	<b>67</b>
6.1	European marks.....	67
6.2	Voluntary national marks .....	68
6.2.1	Austria GPH .....	68
6.2.2	Belgium .....	68
6.2.3	Czech Republic.....	68
6.2.4	Denmark VIK.....	68
6.2.5	Finland VTT .....	68
6.2.6	France ACERMI.....	68
6.2.7	Germany GSH and IVH-BFA.....	68
6.2.8	Greece .....	68
6.2.9	Iceland .....	68

6.2.10	Ireland .....	68
6.2.11	Italy .....	68
6.2.12	Luxemburg .....	68
6.2.13	Malta .....	68
6.2.14	Netherlands KOMO.....	68
6.2.15	Norway.....	69
6.2.16	Portugal.....	69
6.2.17	Spain .....	69
6.2.18	Sweden .....	69
6.2.19	Switzerland .....	69
6.2.20	United Kingdom BBA .....	69
<b>7</b>	<b>References and bibliography .....</b>	<b>70</b>
<b>8</b>	<b>Authors.....</b>	<b>72</b>
<b>9</b>	<b>Alphabetic register .....</b>	<b>73</b>
<b>10</b>	<b>Annex A Tables .....</b>	<b>75</b>

# 1 General

## 1.1 Purpose and scope of this document

As a result of a decision of the European Commission (EC) barriers to trade had to be eliminated. This meant that thermal insulation products, which were chosen as the very first group of construction products, had to be standardised.

The Technical Committee 88 (TC88) of CEN has been dealing with most standards for EPS thermal insulating products, working in Working Group 4 (WG4). Many data have been collected from various countries and new data have been produced to describe the performance of EPS. The large variety of applications all over Europe has been studied and the experiences have been exchanged and recorded. The work in CEN/TC88/WG4 has led to a huge collection of European data, experience and knowledge of EPS products. To make all this information available to producers, designers and users of EPS is the goal of this White Book.

This White Book will also explain the background of the standardisation work, which has led to a specific structure and content of the standards, which follow a common format agreed by CEN TC88.

For EPS several standards have been published and developments still continue. For instance, the subject of ecological assessment and the release of dangerous substances are still under discussion. The standardisation is an ongoing process. Data from research and developments in connection with these projects will be incorporated later. That is why this White Book is a living paper and will be revised from time to time.

In this version of the Whitebook, the following changes are made:

- New information regarding the implementation of the Construction Products Regulations per 01/07/2013, including introduction of new terminology
- Changing (combining) the structure of the EPS standards
- Revision of EPS standards and adding new EPS standards
- Introduction of speaking classes in EN 13163:2012
- Explanation of the Annex for Determination of Reaction to fire of raw materials

## 1.2 New approach of EPS in the market

Beginning of October 2014 the commercial name of EPS has been changed to airpop and is being implemented in most member states. If and when this will have implications on the technical approach of the material in standards and hence the Whitebook and other publications is not known at this moment. Therefore throughout the White book EPS will remain as the name for the material.

## 1.3 Background

In 1985 the European Council published a white paper on completing the internal market for the European Community. The purpose of creating an internal market is to eliminate barriers to trade for products (and services) thus allowing them to be marketed freely through the EU and thereby promote competition. The construction industry, as an important part of commercial activity in the EU, was therefore to become subject to a directive covering construction products - the Construction Products Directive (CPD) - Council Directive 89/106/EEC [5]. The implementation of the CPD was not implemented in all Member States.

Therefore and after evaluation the CPD the European Commission changed the CPD to the Construction Products Regulations (CPR) [55], published 9 March 2011 and in force since 1 July 2013. To clarify the CPR, delegated acts are published on the format and possibilities of a Declaration of Performance and the introduction of Assessment of the Verification of the Constancy of Performance systems for European Assessment documents.

This Regulation is the practical and legal manifestation of freeing the market in the construction sector by making transparent the technical specification of construction products, which are a major part of trade in the construction sector. The CPR only contains ways to declare

characteristics, leaving the required level of a characteristic in end-use condition to the Member States. These levels are generally laid down in National Building Regulations

The CPD introduced the concept of harmonised standards which manufacturers must comply with when placing products on the market. The CPR continues this, with changes compared to the CPD and as from 1 July 2013 with a legal status. In the CPR seven *Basic Requirements* which Building Works must comply with are addressed.

The seven Basic Requirements are :

- 1 Mechanical resistance and stability
- 2 Safety in case of fire
- 3 Hygiene, health and the environment
- 4 Safety and accessibility in use
- 5 Protection against noise
- 6 Energy economy and heat retention
- 7 Sustainable use of natural resources

For Construction Products harmonised technical specifications must be made. When a construction product conforms to the relevant technical specification, the construction works is deemed to be satisfied.

#### *Standardisation*

To obtain harmonised technical specifications all over Europe, European product standards (or European Assessment document) had and sometimes still have to be created. In order to ensure that this work was properly directed to fulfil the Commission's objective with the CPD a Standing Committee for Construction (SCC) had been established (CPD Article 19). Representing Regulators responsible for laws governing construction in the Member States, the SCC determines the properties to be included in the harmonised standards, testing of the products, levels of attestation of conformity to be applied and rules governing labelling and marking.

To support all this activity a range of Interpretative Documents and a series of Guidance Papers have been published to ensure uniformity of interpretation of the CPD.

This standardisation is 'mandated' by the Commission, as advised by the SCC, in support of the CPD. The output must therefore be accepted by the Member States, which are represented in the SCC. The work for the standardisation is through the mandates given to CEN (Comité Européen de Normalisation) or EOTA (European Organisation for Technical Approvals).

- CEN develops mandatory standards (hEN's – harmonised European Standards) for well-known products and/or applications.
- EOTA develops voluntary guidelines (European Assessment documents) for special and/or innovative applications.

For insulation products, the work within CEN is mainly covered by *CEN TC 88 "Thermal insulating materials and products"*, following the mandates M/103, M/126, M/130 and M/138 given under the CPD.

For concrete floor EPS products, the work within CEN is covered by *CEN TC 229 "Precast concrete products"*, following the mandate M/100 given under the CPD.

As from 1 July 2013 the CPR (Construction Products Regulation) has replaced the CPD.

The European product standards were all created to obtain a common European market. The product standards were developed in the various Working Groups (WG's) within TC 88, WG4 developed the standards for EPS for building applications and civil engineering applications, WG10 for building equipment and industrial installations, WG15 for in situ products and WG18 for External Thermal Insulation Composite Systems (ETICS). The product standards for precast concrete products have been and are being developed in the various WG's in TC 229; WG 1 TG 5 has developed the standard for EPS blocks for beam-and-block floor systems

To achieve a common assessment of product performance harmonised European test methods are necessary. All test methods for mechanical and/or physical properties were developed by CEN/TC88/WG1. Other test methods were developed by other TC's (see below at horizontal TC's). Where international standards (ISO) are available, these standards are taken into account according to the Vienna agreement [50].

If a product conforms to a harmonised standard (or European Assessment document), a declaration of performance (DoP) must be made and after that the product must bear CE marking. Having a CE mark, the product it's "passport" to travel freely inside the EC. *The values of the properties measured according to the harmonised test methods may be subject to calculation rules and/or correction factors related to its application.*

*In all European countries where application rules for thermal insulation products were established, these rules had to be revised because they have to refer to the European product standards and to the levels and classes provided there. Figure 1 shows the area of European standardisation and the limit to the remaining field of national standardisation/regulations.*

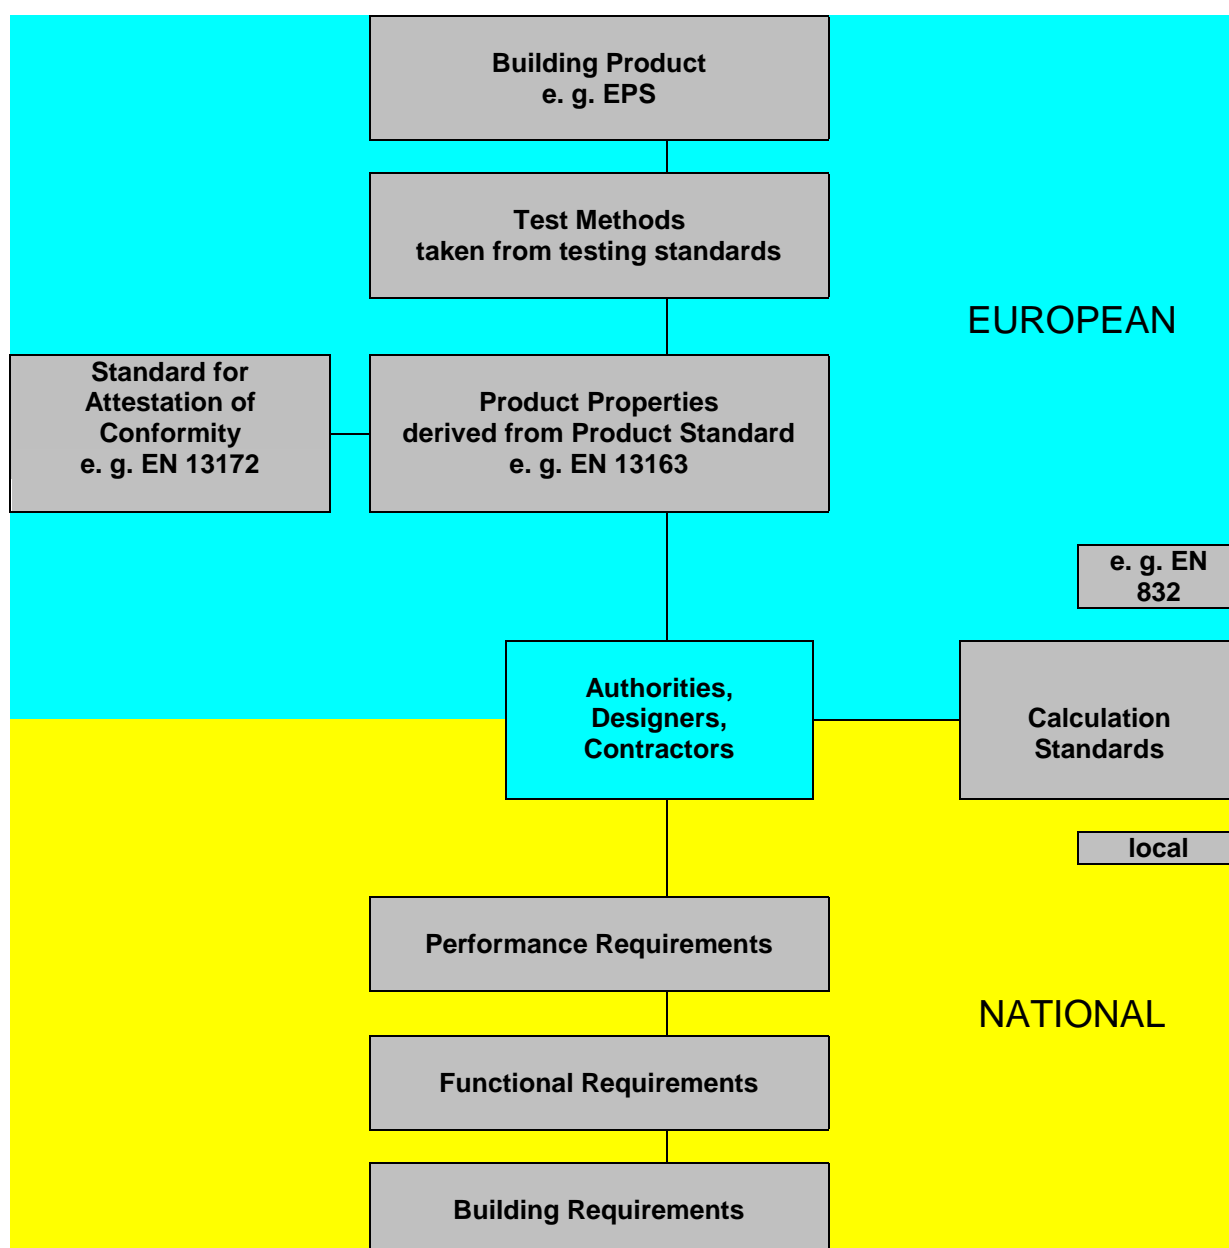


Figure 1: Limitation between European and national standardisation issues. This [Figure 1](#) can be created for every standardised building product.

Beside the product oriented TC's several TC's develop rules to cover aspects for all building products in a "horizontal" way. Those horizontal TC's are:

- TC 89 "Thermal performance of buildings and building components" for calculation methods of the energy performance of products and buildings;
- TC 126 "Acoustic properties of building products and of buildings" for calculation methods of the acoustical properties of products and buildings;
- TC 127 "Fire safety in buildings" for test methods and classification rules for the reaction to fire and fire resistance of products and building constructions;
- TC 350 "Sustainability of construction works" describing methods to determine the sustainability of products and works;
- TC 351 "Construction Products - Assessment of release of dangerous substances".

For EPS the following standards exist:

- EN 13163:2012, Thermal insulation products Factory made products of expanded polystyrene (EPS) – Specification. A package of ten standards for factory made product standards for buildings was developed at the same time and all standards of this package were launched as EN's in 2001 and revised in 2008 and 2012.
- EN 13499:2003, Thermal insulation products for buildings - External thermal insulation composite systems (ETICS) based on expanded polystyrene – Specification. For ETICS two standards were developed and launched as EN's as non-harmonised standards, since no mandate was given at that time. In autumn 2010 a draft mandate was given and the development of a new standard for ETICS (including all possible materials that can be used in ETICS) started. Discussion is still going on about the elaboration of the content of the mandate.
- EN 14309:2009 + A1:2013, Thermal insulation products for building equipment and industrial installations - Factory made products of expanded polystyrene (EPS) – Specification. A package of nine standards for building equipment and industrial installations were developed at the same time and as launched as a package.
- EN 14933:2007, Thermal insulation and light weight fill products for civil engineering applications - Factory made products of expanded polystyrene (EPS) – Specification. For CEA three standards (for EPS, XPS and expanded clay) were developed and launched as EN's.
- EN 15037-4:2010 + A1:2013, Precast concrete products - Beam-and-block floor systems - Part 4: Expanded polystyrene blocks.
- EN 15037-5:2013, Precast concrete products – Beam-and-block floor systems – Part 5: Lightweight blocks for simple formwork.
- EN 16025-1: 2013, Thermal and/or sound insulating products in building construction - Bound EPS ballasting - Part 1: Requirements for factory premixed EPS dry plaster.
- EN 16025-2: 2013, Thermal and/or sound insulating products in building construction - Bound EPS ballasting - Part 2: Processing of the factory premixed EPS dry plaster.

Under development are:

- *prEN 16809*, Thermal insulating products of buildings – In-situ formed products from loose-fill expanded polystyrene (EPS) beads and bonded expanded polystyrene beads – Part 1: Specification for the bonded and loose-fill products before installation.
- *prEN 16809*, Thermal insulation products of buildings – In-situ formed products from loose-fill expanded polystyrene (EPS) beads and bonded expanded polystyrene beads – Part 2: Specification for the bonded and loose-fill products after installation.

Every product standard defines specifications for the product. This includes all relevant properties, how to test and declare these properties, marking and labelling, and the required level of Assessment and Verification of the Constancy of Performance (AVCP). This leaves the required level of a property in end-use condition to the Member States. These levels are generally laid down in National Building Regulations.

The harmonised European product standards contain mandatory parts and may contain voluntary parts. The requirements as mentioned in the relevant mandates are listed in Annex ZA in all harmonised product standards. All standards listed above, except EN 13499 are harmonised. The practical implementation of Annex ZA is mostly given in paragraph 4.2 For all applications in the standards. In the next paragraphs the listed published harmonised standards are explained.



## 2 Explanation of the structure of EPS Standards

### 2.1 Introduction

All EN standards contain ways of determination of properties of products, referring to harmonised EN test methods. The characteristics that have to be declared are given in Annex ZA in the harmonised standards (Essential characteristics). In practice this is more or less translated to characteristics that have to be declared in the clause “For all applications” in the various standards. Most EN standards are written in a similar way, containing the same clauses. These are explained in [2.2](#) to 2.12.

For in situ products, the design of the standards differs: there are two parts, one for the specification of the product and one for the installation. The second part of those standards is not harmonised, since CE marking (and DoP) of the products installed is not the responsibility of the manufacturer. The structure of the in situ standards is explained in [2.13](#). EN 15037-4 differs completely. Its structure is explained in [2.13.3](#).

EN 13163 is the most used standard in the range of EPS standards and the most advanced standard according to the changing CEN rules. Therefore the explanation below is based on this standard and where other standards differ significantly, this will be noted.

The standards are written during the period the CPD was in force and have not yet been adapted to the new terminology listed in the CPR. The CPR is in force since 1 July 2013 and declarations must fulfil the requirements given in the CPR. For readability the headings of the clauses in the explanation below is as given in the standards (CPD terminology), but in the text appears the new (CPR) terminology. In Table 10 the old and new terminology is given.

Table 10: Terminology

<b>Equivalent terms</b>	
CPD	CPR
Essential requirement (ER)	Basic Requirement (BR)
Attestation of conformity (AoC)	Assessment and Verification of Constancy of Performance (AVCP)
Evaluation of Conformity (EoC)	Verification of the Constancy of Performance (VCP)
Declaration of Conformity (DoC)	Declaration of Performance (DoP)
Initial Type testing (ITT)	Product Type determination (PTD)
Factory Production Control (FPC)	Factory Production Control (FPC)
Characteristics	Essential characteristics

### 2.2 Foreword

The foreword gives general information about the creation of the standard. In EN 14309 the Foreword is extended with an extra sub-paragraph, offering contracting parties the possibility to demand properties that are not a part of the standard.

### 2.3 Scope

The scope lists the products covered by the standard and excludes the products not covered by the standard

Composite panels made from EPS and gypsum boards are specified in EN 13950 [\[25\]](#). Self-supporting metal composite panels with an EPS core are covered by EN 14509 [\[26\]](#).

When declared, the minimum thermal resistance is given as 0,25 [m<sup>2</sup>·K/W] and the maximum thermal conductivity as 0,060 [W/m·K] to ensure a minimum thermal resistance. Products having a thermal conductivity of 0,040 [W/m·K] must be at least 10 [mm] thick.

EPS products have a thermal conductivity much lower than 0,060 [W/m·K], typically in the range 0,030 to 0,045 [W/m·K].

EN 14933: For CEA products not always the thermal resistance/thermal conductivity needs to be declared.

EN 14309: The field of application for building equipment and industrial installations covers a temperature range that is applicable for EPS: from – 180 [°C] up to + 80 [°C].

## **2.4 Normative references**

This clause lists in a numerical order all standards which are referred to in the normative part of the standards.

Normally standards are referred to as undated references to avoid revisions of the standards each time a new version of the reference standards is published. The order is EN standards, EN-ISO standards and ISO standards. Dated references are given for prEN's and in the case where specific clauses of a standard are referred to.

## **2.5 Terms, definitions, symbols, units and abbreviated terms**

### **2.5.1 Terms and definitions**

In general EN ISO 9229 [9] contains all definitions. In some cases the standards have a different or additional definition. These are given in this clause.

EPS is divided into 4 types, depending on its application:

- EPS<sub>i</sub>, for load bearing applications where i stands for the declared value (expressed in compressive stress at 10 % deformation).
- EPS S for non-loadbearing applications
- EPS SD for non-loadbearing applications with acoustic properties
- EPS T for floating floor applications
- These definitions only appear in EN 13163 for the time being and are not relevant for in situ standards

Other standards can be useful when discussion on specific items occurs (not referred to in EPS standards):

EN 45020:2007 Standardization and related activities - General vocabulary [10]

EN ISO 13943:2010 Fire safety – Vocabulary [11]

### **2.5.2 Symbols, units and abbreviated terms**

Symbols and abbreviated terms used in the standards are listed in this clause. A complete list of symbols, explanations and units as well as abbreviations is given in Annex A - Tables.

## **2.6 Requirements**

To be recognised as a thermal insulation product, various characteristics must be determined. EN 14933: Sometimes no thermal characteristics are declared for a product for CEA application. Characteristics can be material related or relevant for all applications. Those characteristics are listed in clause 4.2. Depending on a specific application other characteristics may be declared. These are listed in clause 4.3.

Every insulation product according EN 13162 through EN 13171 and EN 16069 has to cover the requirements described in clause 4.2 of the EN's whereas the requirements given in clause 4.3 are optional. These additional requirements will be declared by the manufacturer only if they are needed for the intended use. The application related requirements come from national regulations such as application standards, approvals or others. See also 5.4.2.

EN 13499: This standard deals with external thermal insulation composite systems (ETICS) based on expanded polystyrene. This standard is a product standard specifying a kit of components and it is not an application standard. Since the components are only meant for one application, there is no division of Clause 4 into two parts ("For all applications" and "For specific applications").

A product characteristic is assessed by testing according to a test method. In that test method the minimum number of tests to be performed is given. The product property is the average of the results of those tests. This rule is valid for all requirements where limit values are requested. In cases where statistical evaluation is required, calculation rules are given in Annexes.

## **2.7 Test methods**

To declare the properties of a product the products must be tested. Harmonised test methods are developed and referred to in this clause. Those test methods are to be used; for Factory Production Control purposes alternative test methods can be used. If a dispute with a customer arises, the EN test methods must be used. Additional properties described in Annexes should also use the referenced test methods.

### **2.7.1 Sampling**

General sampling rules are given in the appropriate test method and specific sampling advice may be found in the standards.

### **2.7.2 Conditioning**

Generally no special conditioning is needed for EPS. For some tests and specific conditioning advice may be found in the appropriate testing standard. For determination of the thermal conductivity conditioning is needed, see [3.1](#).

### **2.7.3 Testing**

Measured values which will be used for statistical evaluations shall be single values. It is not allowed to use mean values or use multiple values.

To measure thermal resistance and calculate thermal conductivity there are test methods given as described in [Table 1](#): *Applicable test methods for thermal conductivity*.

Table 1: Applicable test methods for thermal conductivity.

Test method	Title	Guidance, when to be used
EN 12664	Thermal performance of building materials and products – Determination of thermal resistance by means of guarded hot plate and heat flow meter methods – Dry and moist products of medium and low thermal resistance	For all samples with a thermal resistance $R$ : $0,02 \text{ [m}^2\text{K/W]} \leq R < 0,5 \text{ [m}^2\text{K/W]}$
EN 12667	Thermal performance of building materials and products – Determination of thermal resistance by means of guarded hot plate and heat flow meter methods – Products of high and medium thermal resistance	For all samples with a thermal resistance $R$ : $R \geq 0,5 \text{ [m}^2\text{K/W]}$
EN 12939	Thermal performance of building materials and products – Determination of thermal resistance by means of guarded hot plate and heat flow meter methods – Thick products of high and medium thermal resistance	For all thick insulation products (100 [mm] – 150 [mm]), depending on the apparatus used, if the total thickness of the test specimen cannot be measured.
EN ISO 8497	Thermal insulation- Determination of steady-state thermal transmission properties of thermal insulation for circular pipes (ISO 8497:1994)	For pipe sections

## 2.8 Designation code

All products must be accompanied by a designation code. The designation must contain: the abbreviation code (EPS), reference to the standard, classes or levels of the properties of the essential characteristics as given in Annex ZA, as well as the classes or levels of the properties declared according to Clause 4.3 - For specific applications of the standard.

Properties in Clause 4.2 for which only a limit value is required do not appear in the designation code. The producer may specify those properties on the product label or in his literature.

## 2.9 Evaluation of conformity

In the standards, this clause is still given as Evaluation of conformity, but this will be changed into Assessment and Verification of the Constancy of Performance (AVCP) as soon as the standards are amended. The goal of the harmonised product standards is that all insulation products are produced according to their respective product standard, following the prescribed AVCP system. When a product conforms to the standard, a DoP must be made and CE marking must be given. The CE marking enables free trade within the Member states. The rules to declare according to a AVCP system are given in EN 13172.

## 2.10 Marking and labelling

Products must be marked, either on the product, or on the label or on the packaging. The marking must contain the product name or some other identifying characteristic, data from producer or his agent, traceability code, reaction to fire class, declared thermal resistance and/or declared thermal conductivity (where appropriate), nominal dimensions, the designation code (see 2.8) and the number of pieces and area in the package as appropriate. Explanation on CE marking and Declaration of Performance are given in Annex ZA (see 2.11.7).

## 2.11 Annexes

Every standard contains a number of Annexes, some normative, some informative. The normative Annexes are an integral part of the standard, the informative are for information. However, if a manufacturer wants to declare a characteristic according to an informative Annex, it is mandatory to follow the rules given in that Annex.

Annex ZA is informative, however compulsory. It is the legal obligation giving the relation to the CPR (by means of a given Mandate that describes the essential characteristics that have to be declared for CE marking. Annex ZA appears only in harmonised EN's.

Some Annexes are in fact a test method, which is not commonly used and therefore put in an Annex in one or more standards. Those Annexes are explained in 3 Determination of characteristics

### 2.11.1 Annex: Determination of the declared values of thermal resistance and thermal conductivity

For most product standards this Annex is sufficient. EN 14309: Additional measurements must be performed to be able to declare a lambda curve.

#### General

All standards have an Annex to determine the thermal conductivity with a fractile of 90 % of the production and a confidence level of 90 %. Further detailed information about the statistical background is given in [34]. The manufacturer is and remains responsible for the declared values, which are to be expected during an economically reasonable working life under normal conditions. It is not clarified in the standards, but should be at least 25 years.

### 2.11.2 Annex: Initial type testing (ITT) and factory production control (FPC)

Before a product is placed on the market, its characteristics must be determined according to the standard, the Product Type Determination (PTD). After fulfilling the requirements, the product is allowed to be placed on the market. As long as that product is manufactured, a manufacturer must perform Factory Production Control (FPC) to ensure that the declared values do not change and the product shows continuous conformity with the standard.

#### Testing frequencies

The testing frequencies for all properties described in the normative part of the standard are given in two tables: one for Reaction to fire and one for the other characteristics.

When production of a product starts, the characteristics needed for that product must be determined: Product Type Determination (PTD). After fulfilling the requirements, a manufacturer must monitor the characteristics periodically: Factory Production Control (FPC). Products with the same property may be grouped; thus saving costs of testing. Rules for grouping are given in EN 13172.

The Table with testing frequencies for PTD and FPC contains footnotes, some of them need clarification:

- a. The definition of an EPS production unit and an EPS production line is given in EN 13172. Production line: assemblage of equipment that produces products using a continuous process. Production unit: assemblage of equipment that produces products using a discontinuous process.
- b. In cases where the measurements will be statistically evaluated one measurement shall always be one test result.
- c. Product Type Determination (PTD) means that the product characteristics are declared. This must be repeated on a rather low frequency, since product characteristics tend to change in time due to developments in manufacturing.
- d. As soon as test methods for dangerous substances are available the standards will be revised.

**Indirect testing**

Characteristics for which the relationship to another characteristic, e. g. density, is well known, may be tested indirectly via that characteristic. This option will be used if the indirect test is quicker or cheaper. Figures are given for the relationship Compressive stress at 10% deformation versus Density, and Thermal conductivity versus Density.

**Dynamic stiffness**

When dynamic stiffness is required, this must be measured. The dynamic stiffness depends on the thickness of a product. To prevent too much and unnecessary testing, the relation between dynamic stiffness and dynamic elasticity modulus becomes relevant. For a range of thicknesses only the combination of the lowest dynamic elasticity modulus and the dynamic stiffness at the corresponding thickness have to be tested.

Example for testing (when grouping):

Thickness (mm)	Class	Test
40	SD10 - CP3	SD10
50	SD10 - CP3	
60	SD10 - CP3	CP3

**2.11.3 Annex: Product classification**

The various types of EPS can be classified, depending on their intended application: To ensure a certain level of quality of the EPS product Table C.1 in EN 13163, Annex C combines two properties: compressive stress and bending strength. Compressive stress relates to density as shown in Annex B, Figure B.1 of EN 13163. Bending strength depends on the fusion of the EPS product. This combination of compressive stress and fusion quality ensures a good correlation with other properties.

For non-load bearing applications there is no compressive stress required and in these cases EPS S may be used (e.g. in cavity walls and ETICS).

Although EPS T is used for load bearing applications there is no compressive stress required measured according to EN 826. The measurement of a certain level of compressibility according to EN 12431 ensures the load bearing capacity of the product for long time behaviour. The value of the compressibility is approximately the same as the long term compressive behaviour under a floating floor under practical conditions.

**2.11.4 Annex: Multi layered EPS products**

Some products, as EPS, can be combined to two or more layers, developed for a specific application. All test methods as given in the standard apply, only the declaration of thermal resistance and thermal conductivity differs a bit. For multi-layered products the  $R_D$  value is determined on one thickness, the related  $\lambda_D$  is only valid for the measured thickness

**2.11.5 Annex: Verification of the reaction to fire classification of raw materials**

This Annex describes the procedures for raw material suppliers how to get a certificate, which can be used by manufacturers to decrease the frequency of reaction to fire test in Factory Production Control (FPC).

**2.11.6 Annex: Additional properties (informative)**

This annex is informative and provides additional information that is normally not suitable to put in the main body of the standard.

**2.11.7 Annex ZA: Clauses of this European standard addressing the provisions of the EU Construction Products Directive****General**

Annex ZA, in the context of the Construction Product Regulation (CPR), is an informative yet compulsory annex which makes the standard harmonised. Annex ZA is an integral part of the standard.

CE marking in conformity with Annex ZA means that products may be freely placed on the EEA market. Although a product may need to have certain levels of performance to be able to be used in certain end use conditions, a CE marked product cannot be refused access to any EEA market. CE marking will prevent the manufacturer from having to produce different products for different markets and the need for the product to be tested and/or certified again in the country of destination.

Annex ZA identifies which characteristic manufacturers have to declare when placing their products on the European market, both in their own country and in another EC country. The requirement on a certain characteristic is not applicable in those Member States (MSs) where there are no regulatory requirements on that characteristic for the intended use of the product. In this case, manufacturers placing their products on the market of these MSs are not obliged to determine nor declare the performance of their products with regard to this characteristic and the option “No performance determined” (NPD) in the information accompanying the CE marking (see ZA.3) may be used. The NPD option may not be used however, where the characteristic is subject to a threshold level (thermal resistance, thermal conductivity and thickness). Furthermore EPS products having a thermal conductivity greater than 0,060 W/m·K are not covered, which can be seen as a threshold level as well.

Annex ZA establishes the conditions for DoP and CE marking of the products by identifying those clauses of the standard needed to meet the CPR (in sub-clause ZA.1) describing the systems of AVCP in ZA.2, and giving the information that has to accompany the CE mark in ZA.3. A manufacturer has to draw up a Declaration of Performance (DoP) and then he has to affix a CE mark.

### ***Systems of attestation of conformity***

The CPR describes four levels of Assessment of the Verification of the Constancy of Performance (AVCP, former systems of attestation of conformity. AoC), depending on the reaction to fire classification and the way the product is manufactured. The systems vary from a manufacturer's declaration up to systems where a third party is involved in the control schemes (see

Table 2). In all cases the manufacturer must perform Product Type Determination (PTD) and a continuous Factory Production Control (FPC).

***Required level of AVCP***

The reaction to fire classification of the product determines the required level of AVCP. Annex ZA, Table ZA.2 explains the required system of AVCP related to the reaction to fire classification of the product. Table 13 gives the possible systems of the AVCP and the respective tasks for the manufacturer and the notified body.

System 1 and 1<sup>+</sup> is applicable for products with reaction to fire Euroclass A1 up to C inclusive for which in a clearly identifiable stage in the production process results in an improvement of the reaction to fire classification (e.g. an addition to fire retardants). This is normally not applicable for EPS, since almost all converters do not add fire retardants during production process (it is already contained in the raw material). System 3 is generally applicable for all other products, including EPS. System 2+ is generally used for kits or very specific applications (e.g. ETICS, insulation of concrete floors)



Table 2: Tasks of the involved parties for different AVCP levels

Tasks	Steps	Responsible				AVCP 4
		AVCP 1 <sup>+</sup>	AVCP 1	AVCP 2 <sup>+</sup>	AVCP 3	
Initial tests and inspection	Sampling for PTD	NB (M)	NB (M)	M	M	M
	Perform PTDs according to Table ZA.4	NB	NB	NB	NB	M
	Perform further PTDs	NB	NB	M	M	M
	Initial inspection of FPC	NB	NB	NB	M	M
Current surveillance	Current inspections of FPC	NB	NB	NB	M	M
	Collecting samples for product testing	NB	M	M	M	M
	Tests of properties according to Table ZA.4	NB	M	M	M	M
	Test of further properties	M	M	M	M	M
Declaration	Issue of a Certificate of Conformity of products	NB	NB	-	-	-
	Issue of a Certificate of FPC	-	-	NB	-	-
	Issue of a manufacturer declaration for products	-	M	M	M	M
Applications	EN 13163 EN 14309 EN 14933 EN 16025-1				X	
	ETAG 004 EN 15037-4			X		
	Future ETICS Standard			X		
	Voluntary Quality System	X				

**Abbreviations:**

AVCP Assessment and Verification of Constancy of Performance

FPC Factory Production Control

PTD Product Type Determination

M Manufacturer

NB Notified Body (product certification body, production control certification body or testing laboratory)

### ***Third parties***

Member States have appointed notifying authorities with the power to notify bodies for certification, testing and inspection of construction products, to the commission. The same is valid for countries, with which the European Union has concluded agreements (e. g. EEA, MRA, PECA) including such a notification procedure. Member states concerned may only notify bodies within their territories. The minimum requirements for the bodies (TAB's) to be notified are laid down in Annex IV of the CPR. Member States may add requirements for the bodies they notify. Additional requirements can be accreditation of the TAB.

Since the EN standards are written to make a DoP and obtain a CE mark and thus be subject to free trade, one could expect that following the rules a CE mark with an AVCP system 3 would be sufficient. The CE marking can be seen as a passport to cross borders between Member States. The reality of today shows that a voluntary quality system (VQS), including third party control (system 1) is almost inevitable. Sometimes Member States require system 1 for a product or at least one declared property to avoid penalties in the declaration. A VQS is not allowed to interfere with CE marking.

### ***EC certificate and declaration of conformity***

A manufacturer shall draw up a Declaration of Performance (DoP, former declaration of conformity). Examples are given in [“EUMEPS guidance for EPS manufacturers on the Construction Products regulation”](#). The DoP can group products. It must be given in the language of the country of destination and it may appear on a website. However, when a recipient requires a DoP in a paper form, the manufacturer must do so. The DoP has not yet been included in the standards, but an Amendment is in voting procedure. The CPR has come into force on the 1 July 2013, therefore manufacturers must deliver a DoP for each product (or group).

### ***CE Marking and labelling***

The products have to be labelled at least as indicated in Annex ZA, clause ZA.3. Examples are given in [“EUMEPS guidance for EPS manufacturers on the Construction Products regulation”](#).

CE marking is only a part of the labelling a manufacturer must put on his product, label or packaging. The full amount of required data is given in Clause 8 Marking and labelling. Additional voluntary indications may be needed e.g. reference to national application rules. These voluntary indications shall be clearly separated from those belonging to CE marking.

## **2.12 Bibliography**

In the bibliography reference is made to documents that are not included in normative parts of the standard, but can be helpful.

## **2.13 In situ standards**

### **2.13.1 EN 16025-1**

#### ***Thermal and/or sound insulating products in building construction - Bound EPS ballasting - Part 1: Requirements for factory premixed EPS dry plaster***

This standard describes the kind of EPS beads used (virgin or recycled), the bead size, amount of dust and mineral binder. Mortar is added to produce bound EPS beads. During production of beads and mortar coated beads all steps must be monitored.

Only finished products can be tested (thermal conductivity, reaction to fire, compression strength, compressibility, creep, water vapour diffusion resistance, water absorption, dynamic stiffness).

### **2.13.2 EN 16025-1**

#### ***Thermal and/or sound insulating products in building construction - Bound EPS ballasting - Part 2: Processing of the factory premixed EPS dry plaster***

This standard regulates the installation of the Bound EPS beads. This falls under the responsibility of the installer, not the EPS manufacturer.

**2.13.3 EN 15037-4: 2010 + A1:2013,*****Precast concrete products - beam-and-block floor systems - Part 4: EPS blocks***

This standard refers to EN 13163 for the characteristics of the material. For the products tolerances in length, width, thickness and straightness tighter tolerances than given in EN 13163 exist. Mechanical tests on the system determine whether the product is suitable for the intended application.

**2.13.4 EN 15037-5: 2013,*****Precast concrete products - beam-and-block floor systems - Part 5: Lightweight blocks for simple formwork***

This standard is meant for lightweight blocks as formwork where EPS does not contribute more than 50% to the mechanical resistance of the block. For those EPS blocks EN 15037-4 exists.

### 3 Determination of characteristics

The characteristics as listed below do not necessarily appear in the same order in the various standards (mostly the order of EN 13163:2012 is followed), but give an overview of the way the characteristics are to be determined (where applicable).

#### 3.1 Thermal resistance and thermal conductivity

##### **Mechanism of heat transfer**

The mechanism of heat transfer in a thermal insulation layer like EPS can be divided in three components:

- Conductivity
- Radiation
- Mass transfer

More details to be found in ISO 9251 [35]. For radiation see [36] and for mass transfer see [37].

##### **Measurement of thermal resistance and thermal conductivity**

The thermal properties of a sample of insulation board are measured according to EN 12667 or EN 12939 (for boards between 100 and 150 [mm] thickness), taking into account the thickness (measured according to EN 823). The result of the test is the thermal resistance of that specific sample. When the sample is sourced from a product type with no thickness effect and/or is not a multi-layered sample, the thermal conductivity can be calculated using the equation

$$\lambda_{meas} = \frac{d_{meas}}{R_{meas}} \quad [\text{W/m}\cdot\text{K}]$$

Statistical treatment is then necessary to obtain the declared value which must represent 90 % of the production determined with a confidence level of 90 % (90/90). At least 10 measurements must be performed before the statistical treatment can start. Statistical treatment gives an  $R_{90/90}$  and/or  $\lambda_{90/90}$ . When rounded downwards to the nearest 0,05 [m<sup>2</sup>·K/W] for the  $R$  value and upwards to the nearest 0,001 W/(m·K) for the  $\lambda$  value, the  $R_D$  and/or  $\lambda_D$  are determined.

The thermal resistance  $R_D$  shall always be declared for flat products and if possible the thermal conductivity  $\lambda_D$  as well. In most cases the EPS producer will choose to apply the statistics to the thermal conductivity values in one defined product group. He will then state in his official documents the declared thermal resistance  $R_D$  at that thickness and the declared thermal conductivity  $\lambda_D$ .

The declared thermal conductivity is calculated using the equation

$$\lambda_{90/90} = \lambda_{mean} + k \times S_{\lambda} \quad [\text{W/m}\cdot\text{K}]$$

where

$\lambda_{90/90}$  = the 90% fractile with a confidence level of 90% for the thermal conductivity

$\lambda_{mean}$  = the mean value of the measured thermal conductivity

$k$  = number of measurements

$S_{\lambda}$  = standard deviation

The declared thermal resistance is calculated using the equation

$$R_{90/90} = R_{\text{mean}} - k \times S_R \text{ [m}^2 \cdot \text{K/W]}$$

where

$R_{90/90}$  = the 90% fractile with a confidence level of 90% for the thermal resistance

$R_{\text{mean}}$  = the mean value of the measured thermal resistance

$k$  = number of measurements

$S_R$  = standard deviation

Boards and blocks with different shapes than rectangular and planparallel must be made rectangular and flat (uniform thickness) before measuring.

EN 13499: For ETICS, the thermal resistance of the system according EN-ISO 10456 and EN-ISO 6946 is taken into account. The determination of the declared thermal resistance of the EPS product, needed for the thermal resistance of the system, must be performed according to EN 13163.

### **Conditioning**

In EN 13163 rules are given for the conditioning for the determination of the thermal conductivity. This conditioning is needed to prevent an increase of the value of the thermal conductivity after the product has been placed on the market. This conditioning applies for both non-infrared as well as infrared absorbing EPS, but differ. The following procedure is to be used:

Conditioning starts with a minimum of 6 h and a maximum of 3 days. Determine the thermal conductivity according to EN 12667. Store the product for 7 days at 60 °C and 50 °C for EPS T products. Determine the thermal conductivity again. If the results differ less or equal to 1%, the conditioning is deemed to be insignificant. If not, another 7 days of storage at 60 °C (50 °C for EPS T products) and the thermal conductivity must be determined again. Once a manufacturer has determined the conditioning time using a certain raw material, he should record this in his Factory Production Control and does need to repeat the conditioning procedure.

### **Effect of temperature on thermal conductivity**

The thermal conductivity for building products is declared at a mean temperature of 10 °C. For normal building applications this is sufficient. EN 14309: For products that are to be used in a wider temperature range it must be measured at various temperatures (at least three) to establish a curve of thermal conductivity for the declared temperature range. The curve must be verified according to EN ISO 13787. For EPS products only three measurements are needed to determine the curve, since the temperature dependency of the thermal conductivity is linear. For cylindrical products a special test method (EN ISO 8497) has been developed. It is clear that at different temperatures the thermal conductivity varies. The lower the temperature, the lower the thermal conductivity. For products used in building equipment or industrial installations other mean temperatures may be of interest. The thermal conductivity versus temperature is described in reference [20] and shown in [Figure 2](#): Thermal conductivity of EPS versus mean temperature derived from reference [20].

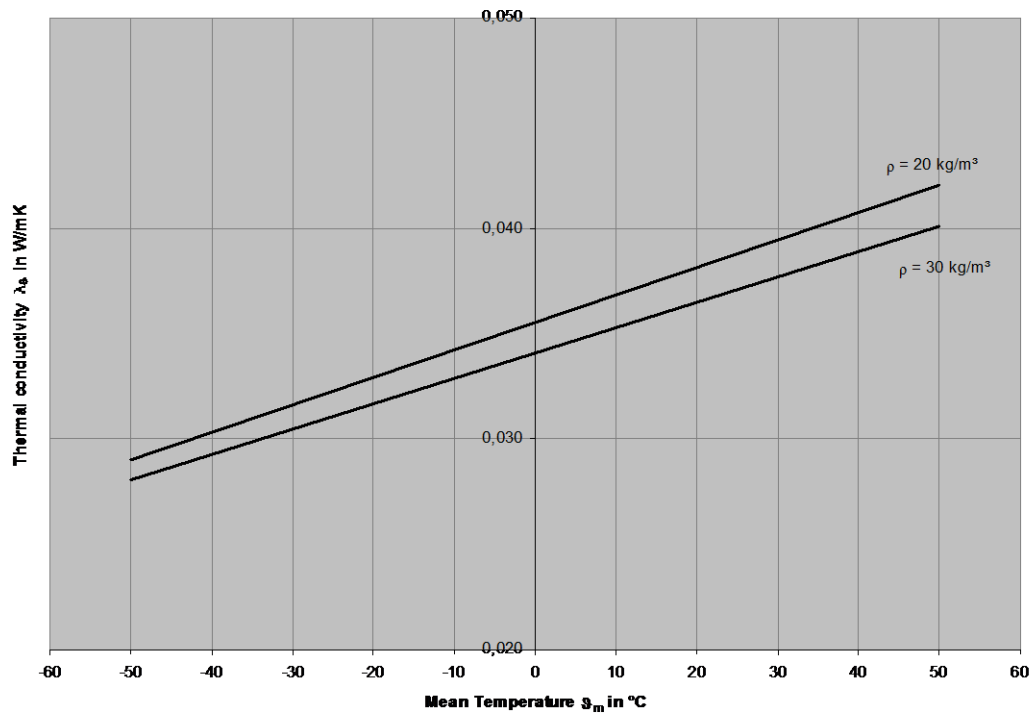


Figure 2: Thermal conductivity of EPS versus mean temperature derived from reference [20].

#### Relation thermal conductivity - density

For non-infrared absorbing EPS (mostly coloured white) there is a distinct relation between thermal conductivity and density, which can be calculated as follows:

Regression for  $8 \text{ [kg/m}^3] \leq \rho_a \leq 55 \text{ [kg/m}^3]$ ;

$$\lambda_{\text{mean}} = 0,025314 \text{ [W/(m·K)]} + 5,1743 \times 10^{-5} \text{ [W·m}^2\text{/(kg·K)]} \times \rho_a + 0,173606 \text{ [W·/(m}^4\text{·K)]}/\rho_a \text{ [W/(m·K)]}$$

$$\lambda_{\text{pred}} = 0,027174 \text{ [W/(m·K)]} + 5,1743 \times 10^{-5} \text{ [W·m}^2\text{/(kg·K)]} \times \rho_a + 0,173606 \text{ [W·/(m}^4\text{·K)]}/\rho_a \text{ [W/(m·K)]}$$

For all types of EPS, non-infrared absorbing -“white”- as well as infrared absorbing -“grey”-, there is a distinct relation between thermal conductivity and density as well as thickness effect which can be calculated as follows:

$$\text{For the regression: } \lambda_{\text{mean}} = b_0 + b_1 \rho_a + \frac{b_2}{b_3/d + b_4 \rho + b_5}$$

where  $b_2$  to  $b_5$  are regression coefficients.

$$\text{For the upper prediction curve: } \lambda_{90/90} = \lambda_{\text{pred}} = \lambda_{\text{mean}} + t_{n-5,95\%} s_{\lambda} \sqrt{1 + \vec{\rho}^T \cdot \vec{C} \cdot \vec{\rho}}$$

### Design values

For use in practice design values,  $\lambda_u$ , must be derived from the declared values,  $\lambda_D$ , taking into account the effects on thermal conductivity according to EN-ISO 10456.

$$\lambda_u = \lambda_D \times F_T \times F_a \times F_m \quad [\text{W}/(\text{m}\cdot\text{K})]$$

Where

$F_T$  is the factor for the thickness effect

Normally for EPS products, having a thickness of at least 50 [mm] and a  $\lambda_D < 0,038 \text{ [W}/(\text{m}\cdot\text{K})]$ , the thickness effect is negligible, the factor being 1. Otherwise this formula must be used:

$$\lambda_{mean} = b_0 + b_1 \rho_a + \frac{b_2}{b_3/d + b_4 \rho + b_5}$$

where  $b_2$  to  $b_5$  are regression coefficients.

$F_m$  is the factor for the moisture effect

For EPS this effect is negligible for normal applications in building construction, the factor being 1.

Specific application, e.g. inverted roofs will have an effect. More information is to be found in [43](#).

$F_a$  is the factor for the ageing affect

For EPS this effect does not occur, the factor being 1

For normal building applications the following formula is valid except for the applications given above):

$$\lambda_u = \lambda_D \quad [\text{W}/(\text{m}\cdot\text{K})]$$

## 3.2 Tolerances on Length and Width, Thickness, Squareness and Flatness

The classes of tolerances for length and width, thickness, squareness and flatness are given in Tables. EN 13163:2012 speaking classes are introduced. This means that the index in the symbol corresponds with the actual tolerance. E.g.  $l_1$  has a tolerance on length of +/- 1 [mm].

All other EPS standards: The tolerance is given in a numerical way. The tables give commonly used tolerances and one or more tighter tolerances which are only needed for specific applications.

EN 14933: Tolerances for dimensions are not always needed in civil engineering applications. Therefore zero classes have been introduced: although for a complete build-up of EPS blocks a certain tolerance will be helpful. Uncut blocks should be avoided.

EN 14309: For building equipment and industrial installations, the pipe section linearity is applicable for cylindrical products and comparable with the requirement on flatness for flat products.

## 3.3 Reaction to fire

### 3.3.1 Reaction to fire classification of EPS products according to the CPR and the harmonised European standards

The CPR refers to basic requirements for construction works. The basic requirements are "translated" by means of Mandates into essential requirements for the products. In the product standards the requirements and classification for reaction to fire are given for the products as placed on the market. Voluntarily producers can determine classification for a number of standardised assemblies representing the end use application.

The package to determine the European reaction to fire classification includes the following test methods:

- EN ISO 1182 Non-combustibility test [32]
- EN ISO 1716 Determination of calorific value [33]
- EN ISO 11925-2 Ignitability test
- EN 13823 Single Burning item (SBI) Test

Results of these tests are used for reaction to fire classification (Euroclasses A1 to F, see Table 3) according to the classification standard (EN 13501-1).

*Table 3: Classes of reaction to fire performance for construction products except floorings and linear products*

Class	Test method(s)	Classification criteria	Additional classification
<b>A1 without testing</b>	EN 13820		
A1	EN ISO 1182 (1); and	$\Delta T \leq 30 \text{ }^{\circ}\text{C}$ ; and $\Delta m \leq 50 \%$ ; and $t_f = 0$ (i.e. no sustained flaming)	
	EN ISO 1716	$PCS \leq 2,0 \text{ [MJ} \cdot \text{kg}^{-1}]$ (1); and $PCS \leq 2,0 \text{ [MJ} \cdot \text{kg}^{-1}]$ (2) (2a); and $PCS \leq 1,4 \text{ [MJ} \cdot \text{m}^{-2}]$ (3); and $PCS \leq 2,0 \text{ [MJ} \cdot \text{kg}^{-1}]$ (4)	
A2	EN ISO 1182 (1); or	$\Delta T \leq 50 \text{ }^{\circ}\text{C}$ ; and $\Delta m \leq 50 \%$ ; and $t_f \leq 20 \text{ [s]}$	
	EN ISO 1716; and	$PCS \leq 3,0 \text{ [MJ} \cdot \text{kg}^{-1}]$ (1); and $PCS \leq 4,0 \text{ [MJ} \cdot \text{m}^{-2}]$ (2); and $PCS \leq 4,0 \text{ [MJ} \cdot \text{m}^{-2}]$ (3); and $PCS \leq 3,0 \text{ [MJ} \cdot \text{kg}^{-1}]$ (4)	
	EN 13823 (SBI)	$FIGRA \leq 120 \text{ [W} \cdot \text{s}^{-1}]$ ; and $LFS < \text{edge of specimen}$ ; and $THR_{600s} \leq 7,5 \text{ [MJ]}$	Smoke production <sup>(5)</sup> ; and Flaming droplets/ particles <sup>(6)</sup>
B	EN 13823 (SBI); and	$FIGRA \leq 120 \text{ [W} \cdot \text{s}^{-1}]$ ; and $LFS < \text{edge of specimen}$ ; and $THR_{600s} \leq 7,5 \text{ [MJ]}$	Smoke production <sup>(5)</sup> ; and Flaming droplets/ particles <sup>(6)</sup>
	EN ISO 11925-2 <sup>(8)</sup> ; Exposure = 30s	$F_s \leq 150 \text{ [mm]}$ within 60 [s]	
C	EN 13823 (SBI); and	$FIGRA \leq 250 \text{ [W} \cdot \text{s}^{-1}]$ ; and $LFS < \text{edge of specimen}$ ; and $THR_{600s} \leq 15 \text{ [MJ]}$	Smoke production <sup>(5)</sup> ; and Flaming droplets/ particles <sup>(6)</sup>
	EN ISO 11925-2 <sup>(8)</sup> ; Exposure = 30s	$F_s \leq 150 \text{ [mm]}$ within 60 [s]	



D	EN 13823 (SBI); and	$FIGRA \leq 750 [W \cdot s^{-1}]$	Smoke production <sup>(5)</sup> ; and Flaming droplets/ particles <sup>(6)</sup>
	EN ISO 11925- 2 <sup>(8)</sup> : Exposure = 30s	$F_s \leq 150 [mm]$ within 60 [s]	
E	EN ISO 11925- 2 <sup>(8)</sup> : Exposure = 15s	$F_s \leq 150 [mm]$ within 20 [s]	Flaming droplets/ particles <sup>(7)</sup>
F	No performance determined or failure to Euro class E		

- (1) For homogeneous products and substantial components of non-homogeneous products.
- (2) For any external non-substantial component of non-homogeneous products.
- (2a) Alternatively, any external non-substantial component having a  $PCS \leq 2,0 [MJ \cdot m^{-2}]$  provided that the product satisfies the following criteria of EN 13823(SBI) :  $FIGRA \leq 20 [W \cdot s^{-1}]$ ; and  $LFS < \text{edge of specimen}$ ; and  $THR_{600s} \leq 4,0 [MJ]$ ; and  $s_1$ ; and  $d_0$ .
- (3) For any internal non-substantial component of non-homogeneous products.
- (4) For the product as a whole.
- (5)  $s_1 = SMOGRA \leq 30 [m^2 \cdot s^{-2}]$  and  $TSP_{600s} \leq 50 [m^2]$ ;  $s_2 = SMOGRA \leq 180 [m^2 \cdot s^{-2}]$  and  $TSP_{600s} \leq 200 [m^2]$ ;  
 $s_3 = \text{not } s_1 \text{ or } s_2$ .
- (6)  $d_0$  = No flaming droplets/ particles in EN 13823(SBI) within 600 [s];  $d_1$  = No flaming droplets / particles persisting longer than 10 [s] in EN 13823(SBI) within 600 [s];  $d_2$  = not  $d_0$  or  $d_1$ ; Ignition of the paper in EN ISO 11925-2 results in a  $d_2$  classification.
- (7) Pass = no ignition of the paper (no classification); Fail = ignition of the paper ( $d_2$  classification).
- (8) Under conditions of surface flame attack and, if appropriate to the end–use application of the product, edge flame attack.

-----  
The SBI criteria are:

- FIGRA = Fire Growth Rate Index
- LFS = Lateral Flame Spread
- $THR_{600}$  = Total Heat Release during the first 600 seconds

Smoke production ( $s_1$  to  $s_3$ ) and the occurrence of burning droplets ( $d_0$  to  $d_2$ ) are additional classifications.

These are based on:

- SMOGRA = Index for rate of Smoke Development (for s-ranking)
- Burning droplets = Occurrence and burning duration of burning droplets (for d-ranking)

In most EU Member States there are no requirements for smoke and flaming droplets/particles for products in Class E.

EPS without flame retardant additive (standard EPS FR-grade) is classified as Euroclass F (without testing). EPS for insulation purposes with flame retardant additive (FR-grade) passes the small burner test (EN ISO 11925-2) at all thicknesses and therefore meets the requirements of Euroclass E. Other classes can be reached for EPS in the SBI test (EN 13823), depending on the thickness, density and mounting & fixing of the samples. These results are only valid for the tested thickness range and the tested mounting and fixing conditions (backing board, type of fixing).

EPS is used in many different applications. If tested as assembly simulating end-use conditions, classes up to B can be reached, depending on the application. For example, EPS in the application behind plasterboard, in a cavity wall or steel sandwich panel can obtain Euroclass B. In EN 15715 (Instructions for mounting and fixing for reaction to fire testing) standardised assemblies simulating end use applications are defined.

The Table for testing on reaction to fire (Annex B of EN 13163) gives minimum product testing frequencies for the reaction to fire characteristics. For EPS boards the ignitability test (EN ISO 11925-2) is the most relevant test. According to footnote h in Table B.2, this test may be

performed once per week, when products are made from certified raw material. In EN 13163 (informative) Annex E verification of the reaction to fire classification of raw materials is included for that purpose. This Annex is based on CEN TR 15985 [52]. Annex E contains tasks for the raw material supplier to obtain a certificate on his raw material. It is written according to CEN rules, only explaining what has to be done and not by whom. When an EPS manufacturer uses a certified raw material, he must ensure that the certificate is valid. When products are made with non-certified raw material, the test must be performed once a day.

If a producer of EPS insulation boards declares class E for his product in the context of CE marking, he has to have regular factory control in place. This means that he has to do daily control of the reaction to fire performance of his products, using the small burner test according to EN ISO 11925-2. If the raw material producer has a certificate, confirming the verification of the reaction to fire, the frequency of testing can be reduced to one test per week or per batch.

The durability of reaction to fire behaviour is covered 3.4. For definitions in the field of fire safety, see EN ISO 13943 [11].

The safety levels in the Member states, representative of a country's building practice and experience in construction and fire, remain their prerogative and are not harmonised. The level of (fire) safety in the individual Member States is laid down in National building regulations referring to European classification and test methods.

A manufacturer or association can have a classification report made for a product in a certain application, in order to save customers time and money to prove that the construction fulfils the requirements of the national building regulations.

### **3.3.2 Behaviour of EPS in the presence of heat and different ignition sources**

On constant exposure to temperatures from 80 °C onwards, EPS softens and shrinks and finally melts. On further exposure to heat, gaseous combustible products are formed by decomposition of the melt. Whether or not these can be ignited by a flame or spark depends largely on the temperature, duration of exposure to heat and the air flow around the material (oxygen availability).

EPS with flame retardants will not be ignited by welding sparks or glowing cigarettes or by small flames. When exposed to a fire source the decomposition products of the flame retardant additive will cause flame quenching so that when the ignition source is removed EPS-SE will not continue to burn.

When tested to ASTM D 1929 [48], the flash ignition temperature in the presence of a pilot flame of standard grade EPS is 360 °C and that of EPS-SE is 370 °C. These values indicate that, when molten EPS decomposes, ignitable gases are only formed at or above 350 °C. In the absence of a pilot flame, the self-ignition temperature of molten EPS is 450 °C.

In the presence of large ignition sources or significant heat fluxes, e.g. greater than 50 kW/m<sup>2</sup> from fires involving other material, EPS with flame retardant will eventually burn, reflecting the organic nature of polystyrene. Burning EPS has a heat release of 40 [MJ/kg (by mass)] [17]. Although the caloric value of EPS is relatively high, the contribution to the fire load is normally limited due to the low density of EPS.

## **3.4 Durability**

### **3.4.1 Durability of reaction to fire against heat, weathering, ageing/degradation**

The long term behaviour of expanded polystyrene classified as 'B1' (hardly flammable) including 'B2' (normally flammable products according DIN 4102 [1] was evaluated [2]. Polystyrene foam boards, containing flame retardants have been used in Europe for construction applications since the 1960's. Since the late seventies, materials classified as 'B1' including 'B2' have been required for these applications in Germany. It was investigated as whether polystyrene foam

boards containing flame retardants maintain their 'B1' respectively 'B2' product characteristic in the long term, or whether ageing occurs, which could result in a change of the classification.

In order to answer this question, the radical burning mechanism of polystyrene and the action of the flame retardants are being summarised. Further, the calculated results of the temperature and time dependent behaviour of the flame retardants that the polystyrene foam contain are given. Additionally the leaching/migration behaviour of the flame retardants in the polystyrene has been experimentally determined. Various West-European EPS raw material producers have gathered laboratory data and results from practice related to the burning behaviour of polystyrene foam boards over a long term.

The report concludes that under the conditions tested no ageing of the flame retardants system used in EPS boards occurs far beyond the normal life span of a building of at least 100 years. So an ageing related change of the 'B1' respectively 'B2' classification does not occur and hence it can be assumed that the relevant Euroclasses established for EPS products are also stable.

#### **3.4.2 Durability of thermal resistance against heat, weathering, ageing/degradation**

EPS does not contain blowing agents that influence the thermal conductivity, only air. Research in Germany and Switzerland show that over a longer period (25 years) the thermal conductivity does not increase [53] [54].

#### **3.4.3 Durability of compressive strength against ageing and degradation**

The durability of compressive strength against ageing is assessed by compressive creep and long term thickness reduction for products used in floating floors. The evidence of the long term compressive behaviour is detailed in [3.10](#).

### **3.5 Dimensional stability**

The classes of dimensional stability are given in Table 2 of EN 13163. The Table gives a class that is commonly used and a class for specific applications. The dimensional stability is also used to prove the durability of thermal resistance against ageing and degradation, see table ZA.1

There is no application rule known in Europe where dimensional stability under specified temperature and humidity is required for EPS. For harmonisation reasons (between the different thermal insulation product standards) this property was adopted in EN 13163. Humidity conditions do not affect the dimensions of EPS.

*Mechanical characteristics are listed as a group in 3.6 to 3.12*

### **3.6 Compressive stress at 10% deformation**

The compressive stress at 10 % deformation ( $\sigma_{10}$ ) is only used to classify EPS products and to obtain reproducible and repeatable test results for factory production control purposes. Compressive strength is normally needed for applications where a load prevails on the EPS e.g. under a floor, on a flat roof, perimeter insulation and so on. The long term deformation (over 50 years) of EPS (compressive creep, see also [3.9](#)) caused by continuous permanent compressive stress should not be above 2%. The maximum allowed load can be found by multiplying the  $\sigma_{10}$  by 0,3, regardless of the material factor  $\gamma_m$ . ([3.14.3](#)).

The compressive strength of EPS is one of the most important properties and therefore it is used to classify EPS products. Classification and relationship with bending strength is described in Annex C of EN 13163. The compressive strength depends directly on the density as shown in Annex B, clause B.2.2 of EN 13163. The relationship between compressive strength and the water vapour diffusion resistance factor / water vapour permeability is given in Annex D, clause D.4 of EN 13163.

Compressive strength depends on the temperature of test which is also described in Table 2. The compressive behaviour at 20 °C is shown in Figure 3:.

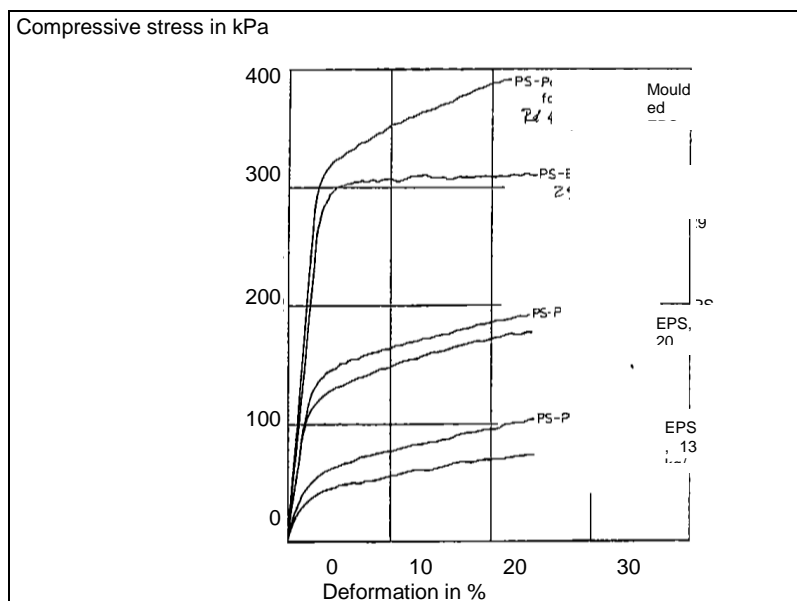


Figure 3:  
Compressive strength at 20 °C of different densities of EPS [21].

Different values of compressive stress at 10 % deformation at different temperatures were measured by Zehendner [21] and given in [Table 4](#).

Table 4: Compressive strength at 10 % deformation at different reference temperatures.

Material	Density	Compressive strength at different temperatures in kPa				
		-170 °C	-60 °C	-30 °C	20 °C	70 °C
EPS block moulded, non flame retarded	14	42	46	58	56	42
	22	210	150	160	160	120
EPS block moulded, flame retarded	14	62	75	77	83	62
	22	190	170	170	160	120
EPS, moulded board	42	510	450	420	360	240

### 3.7 Bending strength

Since bending strength is much easier to determine than tensile or flexural strength it is used for quality control concerning the fusion of the EPS material. For a well fused product bending strength depends on the density as shown in [Figure 4](#): Correlation between bending strength and density..

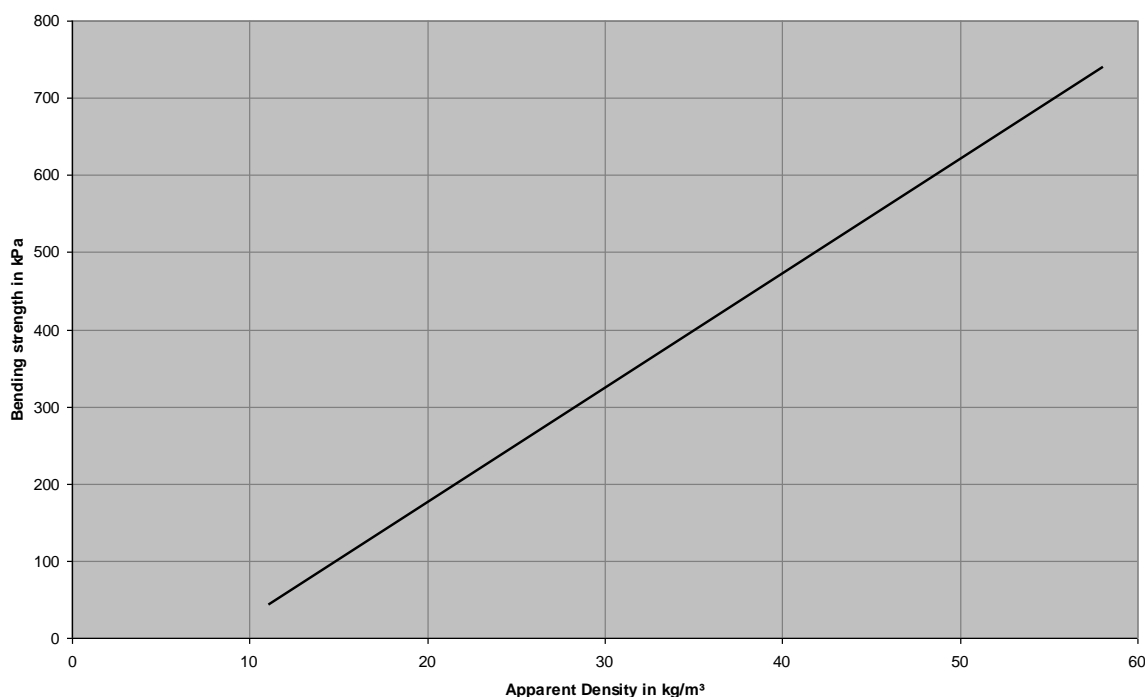


Figure 4: Correlation between bending strength and density.

To calculate the bending strength from density use the equation below.

$$\sigma_b = 14,84\rho_a - 122,6kPa$$

In Annex C of EN 13163 a link between compressive stress and bending strength is given for classification purpose. The figures in Table C.1 do not reflect the real correlation between these properties. The bending strength values in that table represent the minimum requirement for a well fused product. The average bending strength corresponding to compressive stress at 10 % deformation is significant higher than those values given in Annex C, table C.1 of EN 13163.

Different values of bending strength at different temperatures were measured by Zehendner [21] and given in Table 5.

Table 5: Bending strength at different temperatures.

Material	Density	Bending strength at different temperatures in kPa			
		-170 °C	-60 °C	20 °C	70 °C
EPS block moulded, non flame retarded	14	160	220	150	130
	23	290	300	330	290
EPS block moulded, flame retarded	14	200	200	170	130
	22	370	330	280	230
EPS, moulded board	40	690	670	510	300

Relationship to shear strength, see [34](#).

### 3.8 Tensile strength perpendicular to faces

When EPS is subjected to bond stress (caused by the intrinsic weight or wind suction) the tensile strength becomes relevant. For well fused EPS products a relationship between tensile strength and density can be shown, see Figure 5: [\[46\]](#).

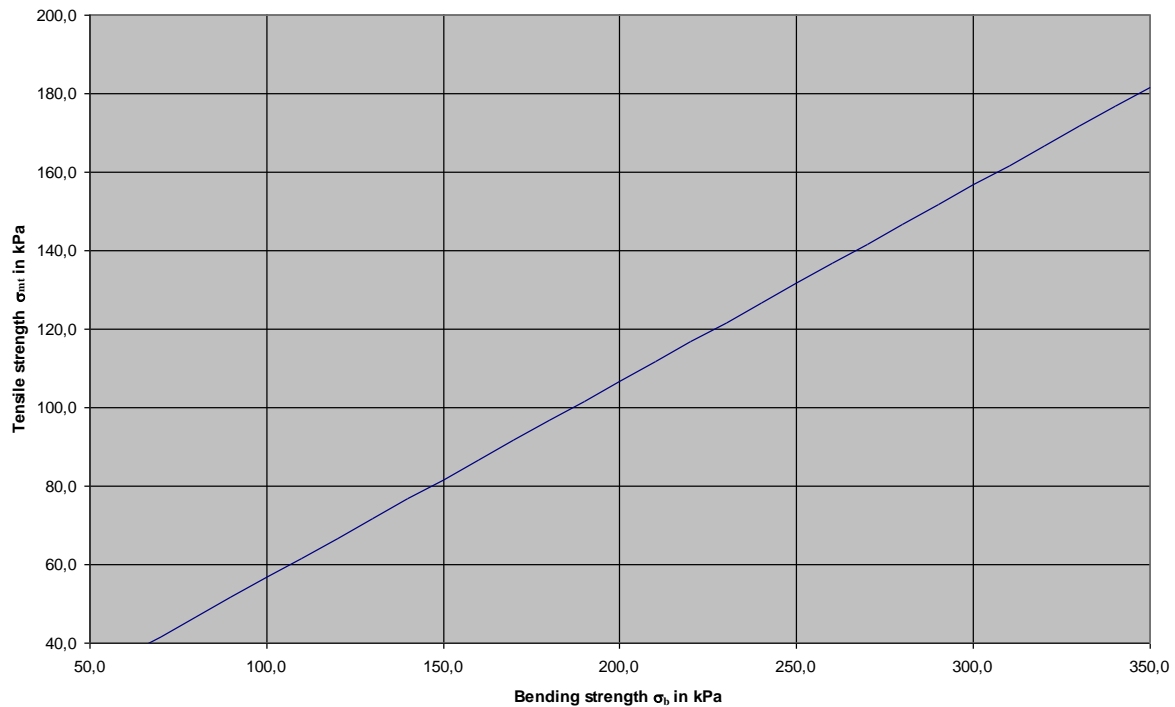


Figure 5:  
Relationship between tensile strength perpendicular to faces and density for well fused products.

$$\sigma_{m1} = 14,00 \cdot \rho - 72,5 \text{ [kPa]}$$

Different values of tensile strength at different temperatures were measured by Zehendner [21] and given in Table 6.

Table 6: Tensile strength at different reference temperatures.

Material	Density	Tensile strength at different temperatures in kPa			
		-170 °C	-60 °C	20 °C	70 °C
EPS block moulded, non flame retarded	14	190	120	120	80
	24	330	400	370	250
EPS block moulded, flame retarded	14	190	190	190	130
	23	320	320	300	210
EPS, moulded board	40	720	790	550	270

### 3.9 Deformation under specific compressive load an temperature conditions

The deformation under specific compressive load and temperature is needed in some countries for applications where pressure and temperature prevail for example on flat roofs.

The measurements from Zehendner [19] show that the pressure-deformation behaviour depends on the environmental temperature.

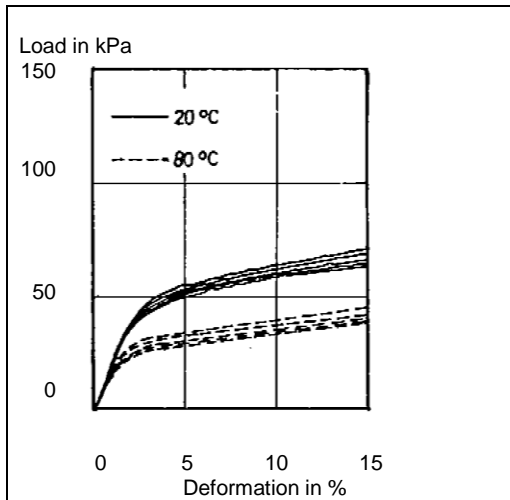


Figure 6:  
Compressive load and deformation of  
non flame retarded EPS, density 14  
[kg/m<sup>3</sup>] [19].

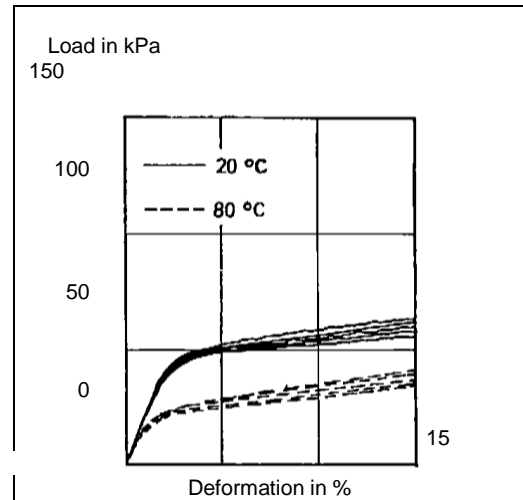


Figure 8:  
Compressive load and deformation of  
flame retarded EPS, density 14 [kg/m<sup>3</sup>]  
[19].

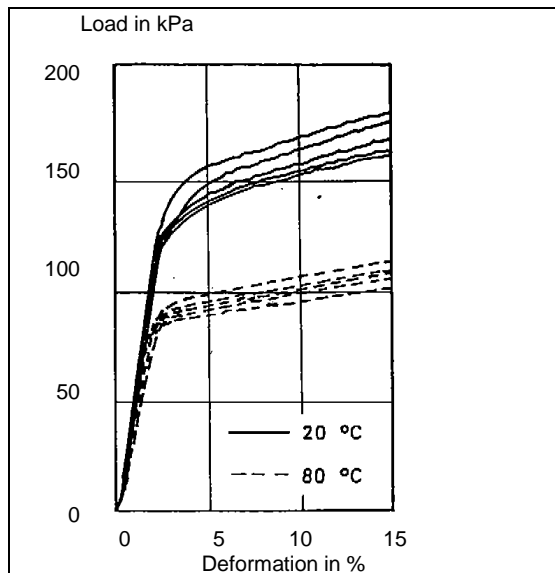


Figure 7:  
Compressive load and deformation of  
non flame retarded EPS, density 24  
[kg/m<sup>3</sup>] [19].

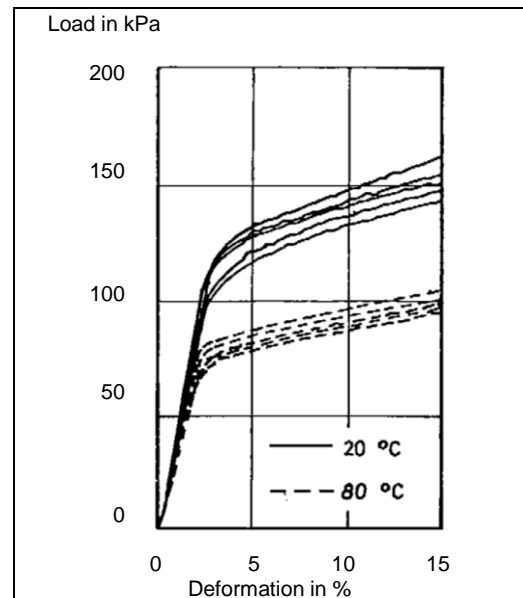


Figure 9:  
Compressive load and deformation of  
flame retarded EPS, density 24 [kg/m<sup>3</sup>]  
[19]

### 3.10 Compressive creep

The long term behaviour under load is determined by compressive creep. Compressive creep is the deformation under a specified load,  $\sigma_c$ , in relationship to the time. Just after the beginning of the load there is an initial deformation  $X_0$ . The total deformation,  $X_t$ , under load can be calculated as follows:

$$X_t = X_0 + 10^a \cdot t^b$$

In this formula  $t$  is used for the time in hours and  $a$  and  $b$  are coefficients which have to be calculated according EN 1606.

Compressive creep will normally be needed for applications where continuous high loads are imposed on a structure supported by EPS, e. g. such as building foundations or cold store floors.

The SP Swedish National Testing and Research Institute in Gothenburg has published results of creep data of EPS in 2001 [28]. SP has measured samples of block moulded EPS of a mean densities of 18,9 [kg/m<sup>3</sup>] and 30,0 [kg/m<sup>3</sup>] over a period of 15.869 h (corresponding to 662 days). The tested compressive stress,  $\sigma_c$ , was taken as a ratio from the compressive stress at 10 % deformation,  $\sigma_{10}$ . The following three different ratios have been tested:

$$q_1 = \sigma_{c1}/\sigma_{10} = 0,25$$

$$q_2 = \sigma_{c2}/\sigma_{10} = 0,35$$

$$q_3 = \sigma_{c3}/\sigma_{10} = 0,45$$

Figure 10 and Figure 11 show the long term creep behaviour evaluated according EN 1606.

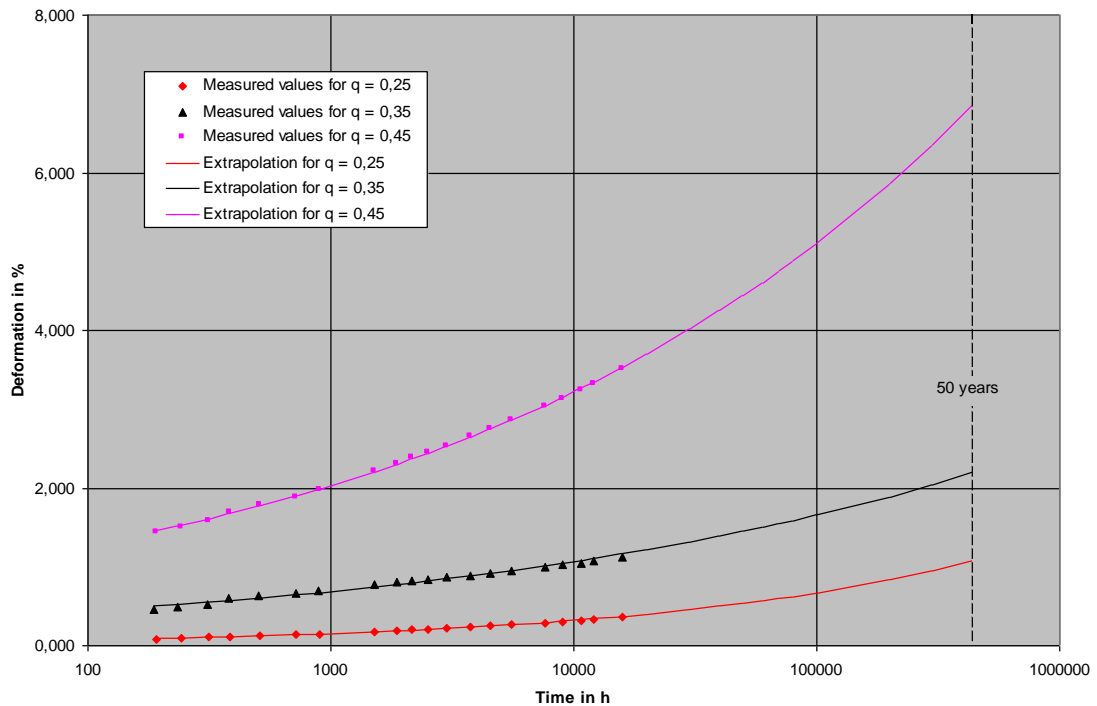


Figure 10:  
Measured total deformation of EPS 100,  $\varepsilon_t$ , and extrapolation to 50 years.



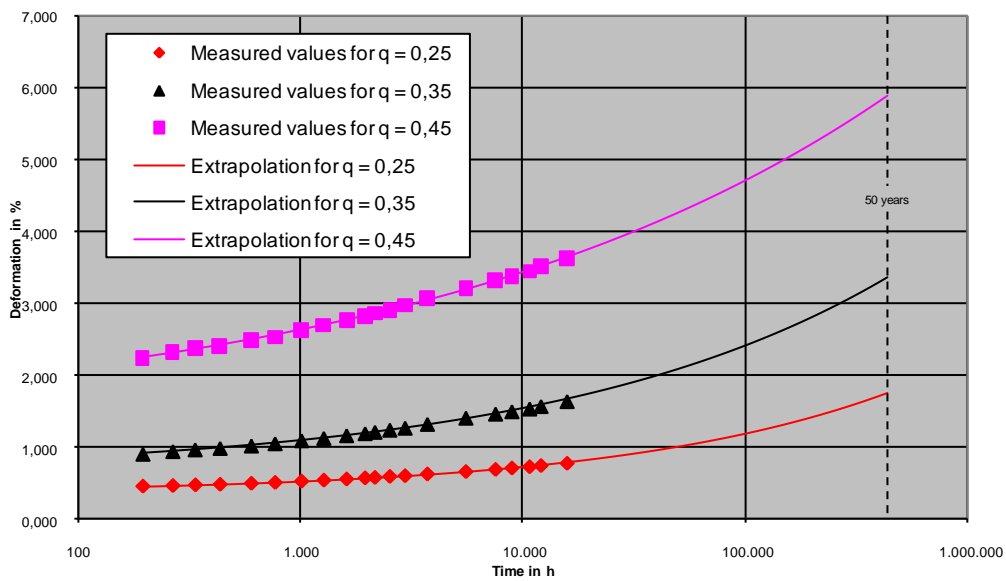


Figure 11:  
Measured total deformation of EPS 200,  $\varepsilon_t$ , and extrapolation to 50 years.

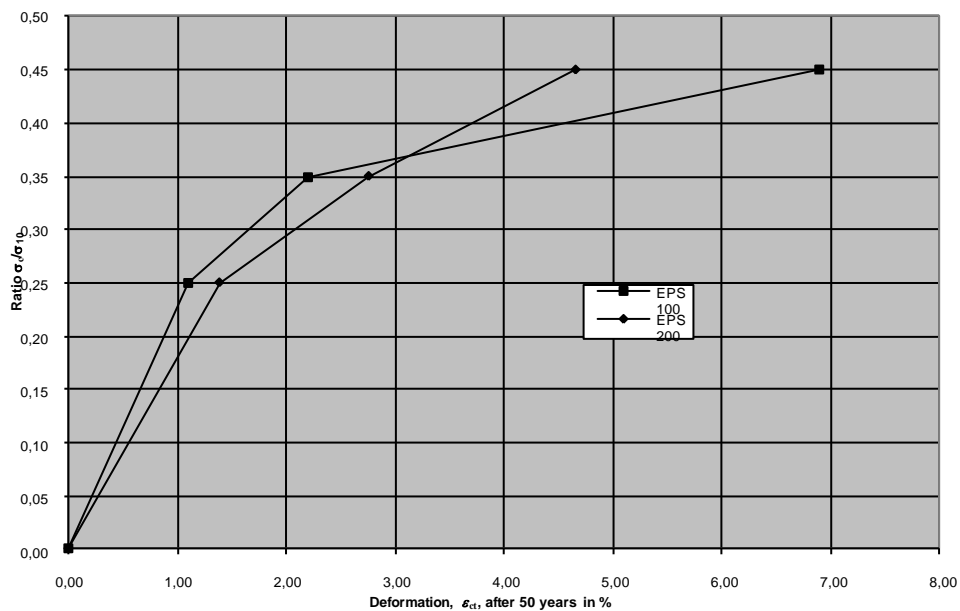


Figure 12:  
Creep compression,  $\varepsilon_{ct}$ , of EPS 100 and EPS 200 after 50 years in relationship to the ratio  $q$ .

To avoid a huge number of measurements for all possible products and practical conditions the ratio  $q$  may be used to declare the correct compressive stress,  $\sigma_c$ , which leads to a deformation of 2 % after 50 years. According to Figure 12 this ratio is about 0,30 which proves that the factor of 0,30 given in D.2 of EN 13163 is correct.

The initial deformation derived from the measurements from SP are for a ratio of 0,30 as follows:

EPS 100 0,54 %  
EPS 200 0,48 %

**Example**

An EPS insulation shall be designed for the use under a foundation which will impose a compressive stress of 75 kPa. The deformation of 2 % shall not be exceeded. Which material has to be chosen?

$$\sigma_c = 75 \text{ [kPa]}$$

$$\sigma_{10} = \sigma_c / q = 75 \text{ [kPa]} / 0,30 = 250 \text{ [kPa]}$$

That means an EPS material of  $\sigma_{10} = 250 \text{ [kPa]}$  has to be chosen for this application. To decide on the apparent density,  $\rho_a$ , which has to be selected the equation B.2 of EN 13163 (Annex B) may apply:

$$\sigma_{10, \text{pred}} \approx 10,0 \text{ kPa} \cdot \text{m}^3/\text{kg} \times \rho_a - 109,1 \text{ [kPa]}$$

$$\rho_a = (\sigma_{10, \text{pred}} + 109,1 \text{ kPa}) / 10,0 \text{ [kPa} \cdot \text{m}^3/\text{kg}]$$

$$\rho_a = (250 \text{ kPa} + 109,1 \text{ kPa}) / 10,0 \text{ [kPa} \cdot \text{m}^3/\text{kg}]$$

$$\rho_a = \underline{35,9 \text{ [kg/m}^3\text{]}}$$

The compressive creep of a product designed in such a way would have a declared value of CC(2%/1,5%,50)75.

If the producer uses a specific proven correlation of compressive stress and density this may be applied which may lead to other results.

EN 1606 is the harmonised test method to determine compressive creep. For EPS mostly a simpler method is used, a tabulated value as given in [50]. EPS products ensure a maximum creep value of 2 % over a predicted 50 year period.

**3.11 Shear behaviour.**

The shear behaviour may be useful in cases where EPS is laminated and where EPS contributes to the mechanical performance of the element. The shear strength of EPS depends on the quality of fusion and on the density. For well fused products the correlation between shear strength and density is given in [Correlation between](#) shear strength and density..

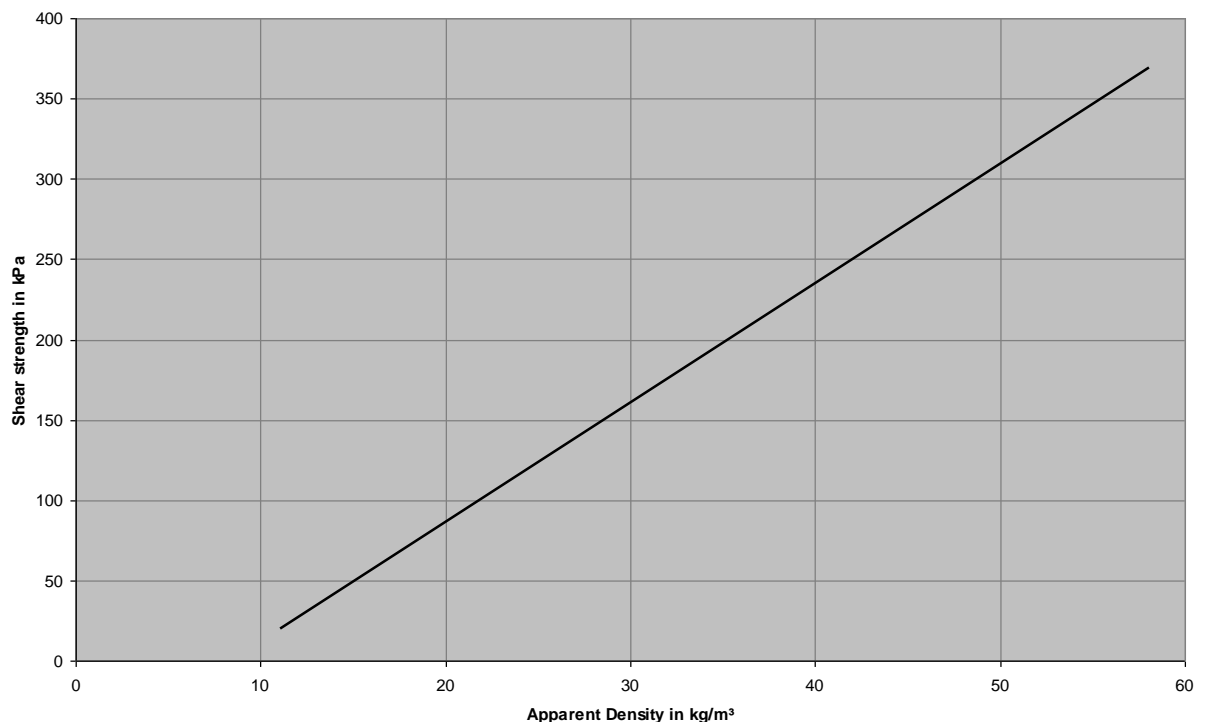


Figure 13: Correlation between shear strength and density.

$$\tau = 7,43\rho_a - 62,8 [\text{kPa}]$$

Different values of shear strength at different temperatures were measured by Zehendner [21] and given in [Table 7](#).

Table 7: Shear strength at different temperatures.

Material	Density	Shear strength at different temperatures in kPa	
		20 °C	70 °C
EPS block moulded, non flame retarded	14	550 – 1.000	280 – 410
	23	770 – 1.100	560 – 850
EPS block moulded, flame retarded	14	820 – 1.300	350 – 380
	22	670 – 1.300	530 – 750
EPS, moulded board	40	1.300 – 1.500	1.000 – 1.100

More data are to be found in [46]. In literature [46] a relationship between shear strength and bending strength is shown, see [Figure](#).

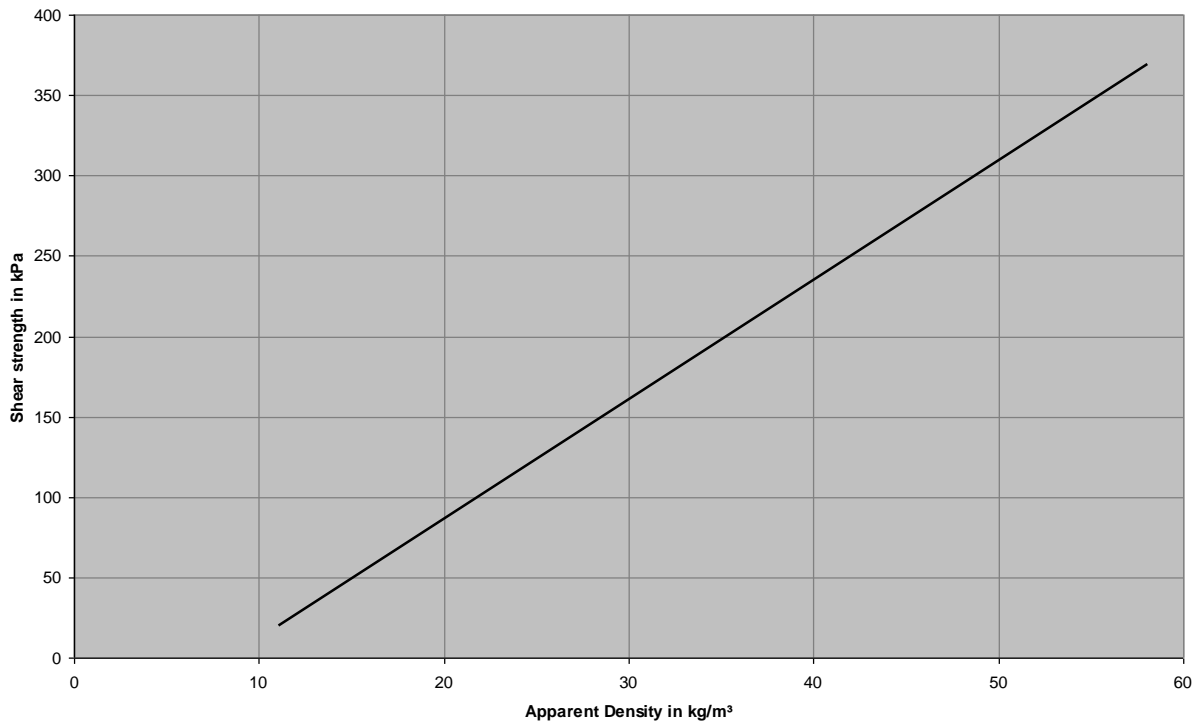


Figure 14: Relationship between shear strength and bending strength.

$$\tau = 6,7 \text{ kPa} + 0,5 \cdot \sigma_b$$

### 3.12 Behaviour under cyclic loading

When subjected to a cyclic loading EPS can be tested according to EN 13793. The deformation (in %), the number of load cycles and the stress (in kPa) is then to be declared. Cyclic loading is relevant in flat roof (walkability) and civil engineering applications.

For CEA applications the test method is already suitable, for flat roof applications it needs to be adapted. See also [3.14.4](#)


*Special for CEA applications the compressive behaviour is listed in 3.13 and 3.14.*

### 3.13 Compressive stress at 2 % and/or 5 % deformation

For specific applications determinations of 2 % and/or 5 % can be relevant. The calculation of the stress at those deformations must be done according to EN 826, although only the calculation at 10 % deformation is given in EN 826.

Note: on the basis of 10.000 test carried out by BASF an arbitrary relationship has been introduced in this standard between the strength at 2%, 5% and 10% deformation - the designation strength. This enables producers in the tender phase to quickly designate the requested compressive strength/ product type.

On the basis of the BASF-research the three tables in EN 14933 have been developed and incorporated. The relationship between stresses and strains are given in the next diagram.

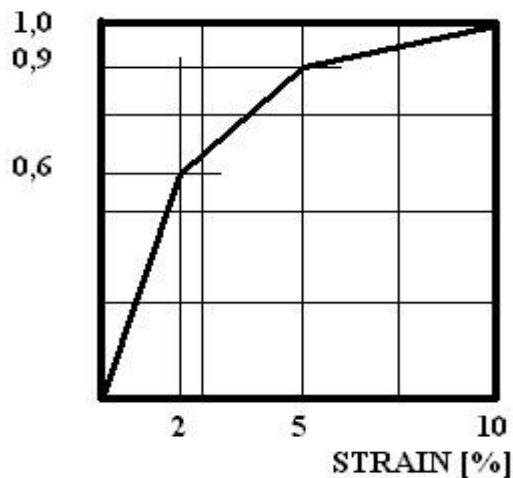

This implies, that if a contractor/ consultant orders EPS with a compressive strength of 90 kPa at 2% deformation, in regular cases a EPS product- type of  $90/0,6 = 150$  [kPa] fulfils the requirements.

### 3.14 Product properties of EPS and Eurocodes

#### 3.14.1 Short-term compressive strength

The stress/strain curve of EPS has a particular shape and resembles very much the stress/strain curve of wood products. Creep that appears at long term load at a certain stress level up to  $9/16$  of the short term compressive strength will and be reduced to zero in the end. When the stress level at the beginning is too high, progressive collapse will show rather quick. The relation is given in Figure 17.

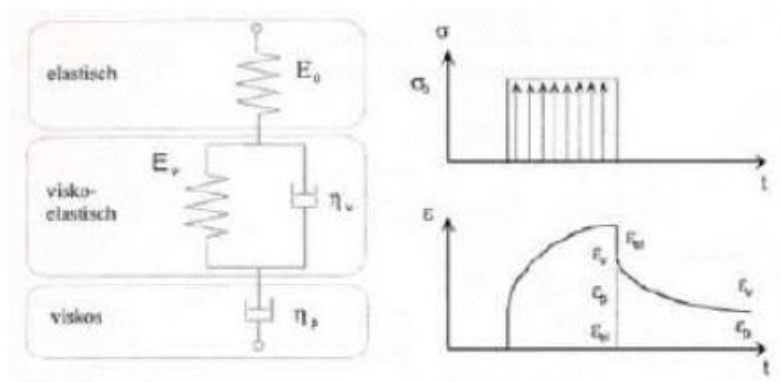


Figure 17 Stress/strain curve of EPS 100

When in accordance with EN 826 the compression strength is determined, the linear – elasticity limit (or proportionality limit) will be reached at 1 – 1,5 % deformation. For compression strength, as defined in EN 826, a value at 10% deformation is commonly used. This  $\sigma_{10}$  characteristics is used as product classification. When tested according to EN 826, the speed of compression is approximately 10 % of the thickness of the sample per minute. This initially linear-elastic deformation is used to determine the tangent modulus  $E_t$  [kPa]. Figure 20 shows the stress/strain relation for the rest of the section of the test.

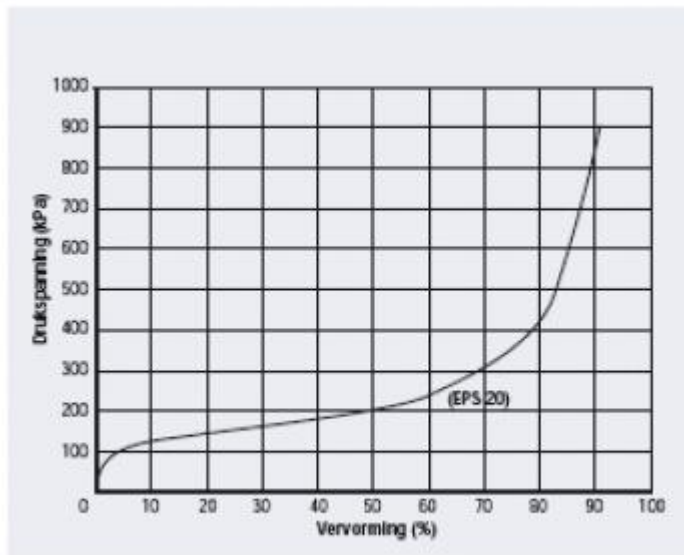


Figure 1: Last-vervormingsdiagram.

Figure 20 Stress/deformation curve of EPS (initial)

In this second part one can already see the non-linear elastic stress/strain development. In Figure 21 is shown how the first part of the section develops and how the "yield" is defined. This yield is approximately 75 % of the compressive stress, at all types of EPSi. The requirement on short term compressive strength, determined at 10 % deformation, is declared in the CE mark.

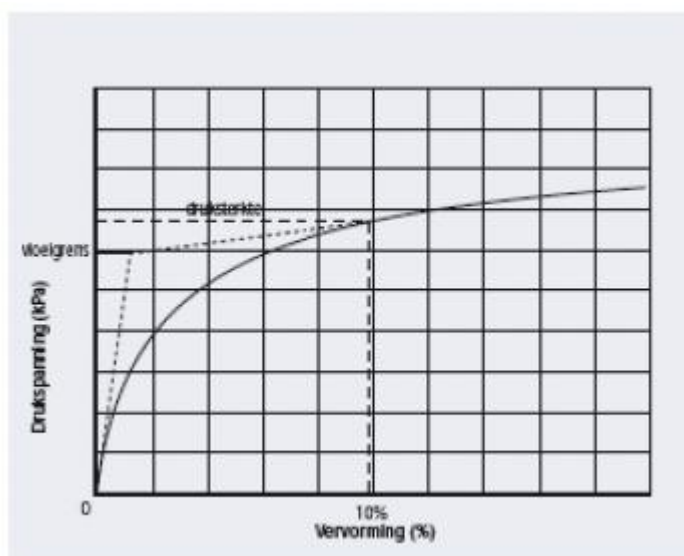


Figure 21

The third section is created by reinforcing behaviour as a result of the compression of the structure of the beads, up to ca. 25 % at EPS 60 to 50 % at EPS 300. When a product has a deformation of ca 70 %, a one sided fracture occurs and EPS becomes hard polystyrene. According to Eurocode 7 (EN 1997-1) a material factor ( $\gamma_m$ ) = 1,1 must be introduced to determine the design value of the short term compressive strength  $\sigma_{10}$ . Example for EPS 100:  $\sigma_{10,d} = 100/1,1 = 90$  [kPa]. This value is given in CROW Richtlijn "Lichte ophoogmaterialen" chapter 5.4.2, edition 2013 [56].

### 3.14.2 Creep and relaxation

Creep is the phenomenon where the deformation increases with time as a result of a certain load. For EPS there are five independent variables: density, stress, deformation, time and temperature. The same goes for relaxation, the phenomenon where at a given deformation the (internal) stress decreases with time. An example is given in Figure 22: the time/deformation curve of EPS 150 ( $\rho = 23,5$  [kg/m<sup>3</sup>]) at three stress levels (30, 50 and 70 [kPa]), at a (laboratory) temperature of 23 °C over a period of 500 days.

This curve can also be given as the stress/deformation diagram at various times (Figure 23).

Conclusion: the deformation at long term stress at approximately 25 % of the short term stress, is maximum 1 % and creep is negligible.

In calculations the EN standards are applied: at a stress level of ca.  $0,3^* \sigma_{10}$ , the total deformation will be 2 % after 50 years. Research has shown that the expected creep of EPS 60 and EPS 100 at a stress of approximately 25 % of the short term compression strength after one year is less than 0,2 %. Half of the creep behaviour occurs after one day. The creep behaviour on a logarithmic scale is linear. The initial deformation is ca. 0,5 %. Over a period of 50 years this comes down to a total of 2,5 %.

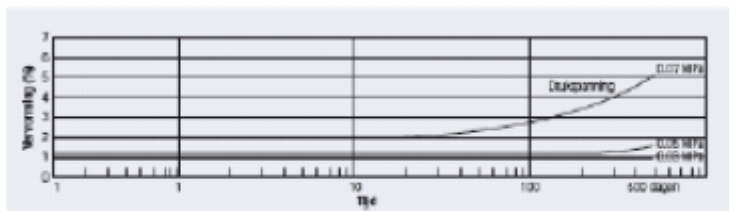


Figure 4: Time/deformation curve of EPS 150

Figure 22 Time/deformation curve of EPS 150

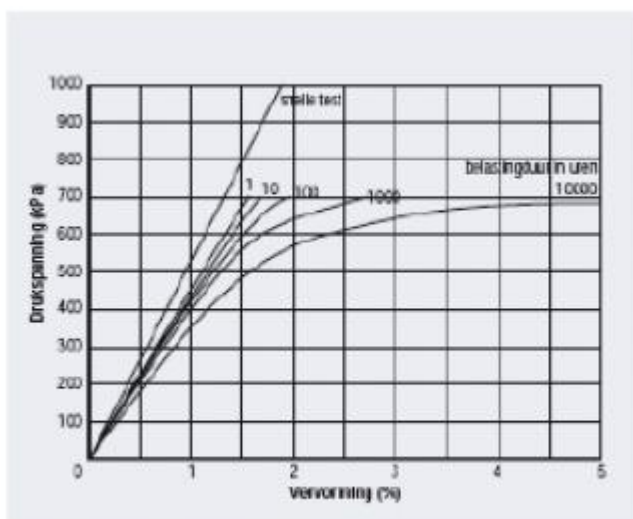


Figure 5: Stress/deformation diagram at various times

Figure 23

### 3.14.3 Long term compressive strength

The long-term compressive strength is the continuous permanent admissible stress level over a period of 50 years, to prevent unwanted creep effects. Based on the creep-relaxation effects, the long term compressive strength of EPS is set on  $0,3 \times$  short term compression strength.

To determine the design value of the long-term compressive strength,  $\sigma_{10;perm;d}$ , according to EN 1997-1 a material factor must be taken into account:  $\gamma_m = 1,1$ .

Example: EPS 100:  $\sigma_{10;perm;d} = 0,3 \times 100 / 1,1 = 27,3$  [kPa].

Values are given in Table 15.

### 3.14.4 Modulus of elasticity

Assuming that EPS in CEA applications will have a maximum deformation of 1%, the relation of the short term tangent modulus applies, as given in Figure 24.

In formula:  $E_t = 0.045 \rho - 3$  [MPa]. As a result of that the calculation values used in Europe are given in Table 15.

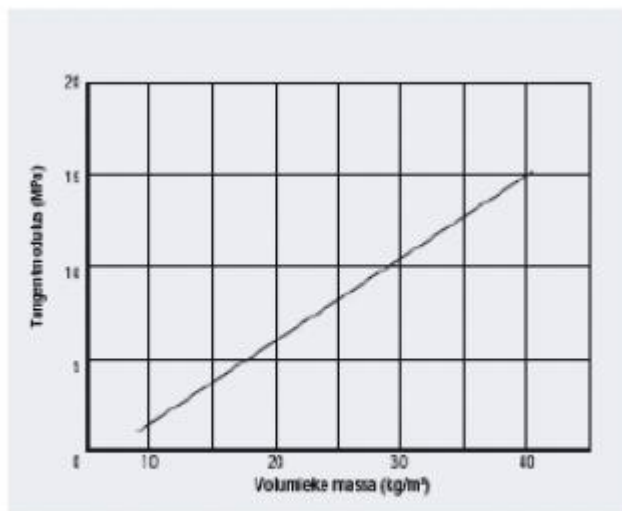


Figure 24: Relatie tangentmodulus/volumieke massa.

Figure 24 Short term tangent modulus

### 3.14.5 Compressive strength under cyclic load

Based on extensive studies it has been concluded that, with a relative light permanent loading at the top ( $15 \text{ [kN/m}^2\text{]}$ ) and if the deformation under a cyclic load remains under 0,4% that deformation will be elastic and there will be no permanent deformation. Translated into stresses the maximum safe value due to cyclic loading is  $0,35 \times \sigma_{10}$ . This value has been recalculated from Duskov<sup>1</sup> thesis. Thus the declared compressive strength under cyclic load  $\sigma_{10;cycl;d} = 0,35 \times \sigma_{10}$  (e.g. for EPS 100:  $\sigma_{10;cycl;d} = 0,35 \times 100 = 35$  [kPa]). For the calculation of the design value  $\sigma_{10;cycl;d}$  the material factor ( $\gamma_m$ ) has to be taken into account (according to EN 1997); this factor ( $\gamma_m$ ) is 1,1 (e.g. for EPS 100:  $\sigma_{10;cycl;d} = 35 / 1,1 = 31,8$  kPa).

Apart from the test method EN 13793 which is the usual one for road building in case of any defined property for dynamic resistance and referred to in EN 13163, in the EPS standard for civil engineering applications another test method, SP 2687, a dynamic load test has been developed for railroad applications in the Nordic countries [27].

<sup>1</sup> Duškov, Milan: EPS as a light weight sub-base material; 1997 Delft NL

Table 15: EPS properties for CEA

EPS product type according to EN 14933							
Description	Symbol	Unit	EPS type				
			EPS 60	EPS 100	EPS 150	EPS 200	EPS 250
Declared short term compression strength	$\sigma_{\varepsilon=10\%}$	[kPa]	60	100	150	200	250
Design short term compression strength	$\sigma_{\varepsilon=10\%;d}$	[kPa]	54,5	90,9	136,5	181,5	227,3
Modus of elasticity	$E_t; E_{dyn.}$	[kPa]	4000	6000	8000	10000	12000
Declared long term compression strength	$\sigma_{\varepsilon=10\%;perm}$	[kPa]	18	30	45	60	75
Design long term compression strength	$\sigma_{\varepsilon=10\%;perm;d}$	[kPa]	16,4	27,3	40,9	54,5	68,2
Declared strength under cycling loading	$\sigma_{\varepsilon=10\%;cycl}$	[kPa]	21	35	52,5	70	87,5
Design strength under cycling loading	$\sigma_{\varepsilon=10\%;cycl;d}$	[kPa]	19,1	31,8	47,7	63,6	79,5

Note: this relationship is based on testing of materials over several decades; if a producer is able to prove (certified) better data for his specific products, this "better" result can be taken into account.

*Mechanical characteristics for ETICS applications are listed from 3.15 to 3.20*

### 3.15 Mechanical resistance and stability of the system

Various aspects of the mechanical properties of the system must be declared, depending on fixing by adhesive or mechanical fixing. For fixing by adhesive: The bond strength of the base coat to the EPS board as well as the bond strength of the adhesive must be at least 80 [kPa], according to EN 13494. For mechanical fixing: the pull-off resistance of the ETICS must be determined according to EN 13495. The test result, combined with the applied forces (wind load) on the system, determines the amount of needed anchors.

### 3.16 Tensile strength of the reinforcement

The tensile strength of the glass fibre meshes shall be determined in accordance with EN 13496. The following requirements shall be satisfied:

- the mean value of the tensile strength shall be greater than 40 [N/mm] and no individual value shall be less than 36 [N/mm] at the initial state;
- the relation of the tensile strength to the elongation at failure, stored under normal conditions and in aggressive medium, shall be not less than 1 [kN/mm];
- the tensile strength after storage in aggressive medium, in accordance with EN 13496, shall be greater than 50 % of the initial tensile strength.

### 3.17 Resistance to impact

The system must be tested according to EN 13497. Two levels can be declared: Level I 2 (no damages at 2 [J]) and I 10 (no damages at 10 [J]).

### 3.18 Resistance to penetration

The system must be tested according to EN 13498. Two levels can be declared: Level PE 200 (> 200 [N]) and PE 500 (> 500 [N]).

### 3.19 Durability and adhesion of the finishing material on the base coat

After conditioning according to EN 1062-11, samples of the system must be tested according to EN 4628-2, EN 4628-4 and EN 4628-5. The way the results are interpreted is given in clause 4.11 of EN 13499.



### 3.20 Conditioning of the test specimen in accordance with EN 1062-11

For the determination of the tensile bond strength of the base coat to the thermal insulation material, liquid water permeability of the system surface, resistance to impact, resistance to penetration, water vapour permeability, durability and adhesion of the finishing material on the base coat. This clauses explain the conditioning according EN 1062-11, which is needed for the determination of the durability and adhesion of the finishing material.

*Moisture behaviour is listed from 3.20 to 3.26*

### 3.21 Water absorption

EPS has a good resistance against water absorption. Therefore the short term water absorption test does not appear in the EPS standards

For normal building applications the water uptake of EPS is negligible, The different test methods for water absorption are accelerated tests to describe the material but the results may not directly be relevant for design purposes. For common applications the design thermal conductivity,  $\lambda_U$ , is the same as the declared thermal conductivity,  $\lambda_D$  (see 3.1).

In applications where the EPS product is in permanent contact with water, the moisture conversion factor of the thermal conductivity should be estimated according to EN ISO 10456.

Water absorption can be measured short term or long term, by partial or total immersion or by diffusion.

The change of thermal conductivity with moisture content from thermal insulation and other construction materials was determined by a German research [49]. This literature shows that EPS has a much more favourable behaviour concerning the increase of thermal conductivity than other insulation materials having no closed cell structure. To calculate the relationship between moisture content and thermal conductivity for different densities the factor  $F_\Psi$  was introduced by the authors of this research. The equations below present this relationship more precisely than the values given in [Table 8: Thermal conductivity in relationship to moisture content according ISO 10456](#). and [Table 9](#).

NOTE: The factor  $F_\Psi$  is referred to as  $F_m$  in EN-ISO 10456.

$$F_\Psi = \lambda_u / \lambda_{u=0}$$

Where  $u$  is the variable water content in vol-% and  $\lambda_{u=0}$  is the thermal conductivity of a dry material.

$$F_\Psi = 1,0 + 0,032078 \cdot u + 0,0010031 \cdot u^2$$

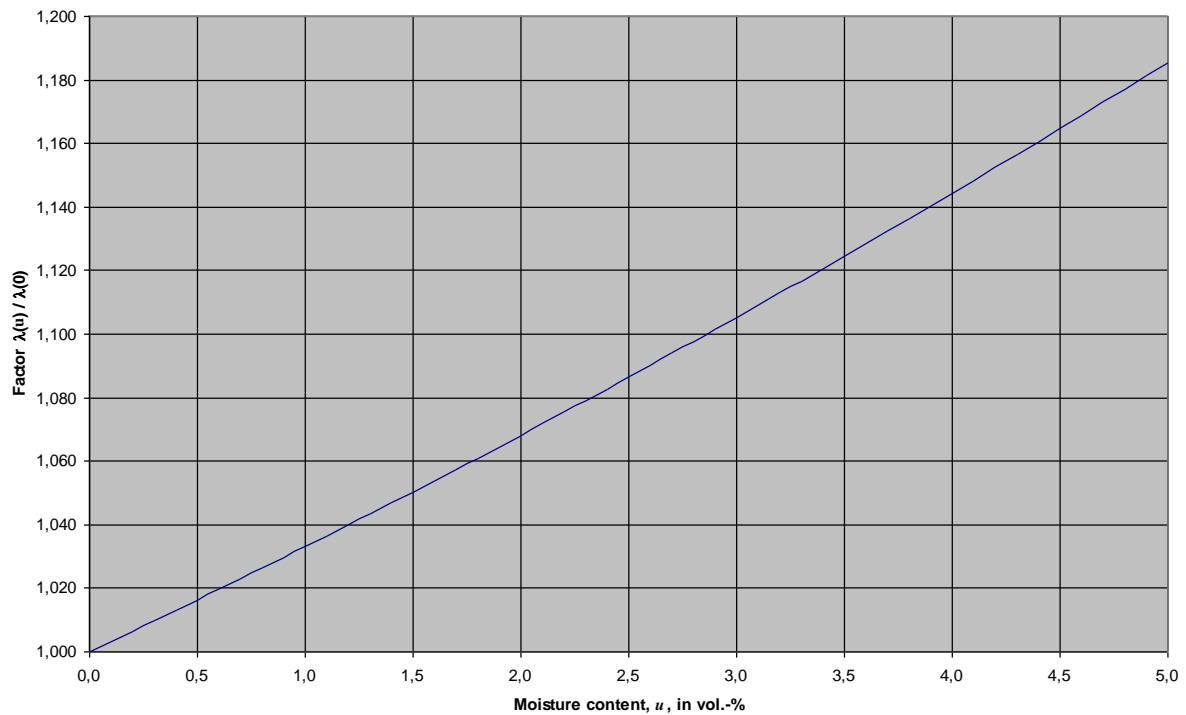


Figure 15: Change of thermal conductivity with moisture ref. [49].

Table 8: Thermal conductivity in relationship to moisture content according ISO 10456.

Moisture content %	Design thermal conductivity ( $\lambda_u$ )	
	$\lambda_D = 0,033 \text{ W/mK}$	$\lambda_D = 0,036 \text{ W/mK}$
1,0	0,034	0,037
2,0	0,036	0,039
3,0	0,037	0,041
5,0	0,040	0,044
10,0	0,049	0,054
15,0	0,060	0,066

### Example

In drained building foundations where the EPS product is against or within the ground, the practical long term water content,  $W_p$ , is approximately

$$W_p \approx W_{lt} / 2$$

and in non drained foundations

$$W_p \approx W_{lt}$$

According to the levels given in EN 13163 (Table 12) the design thermal conductivity may be calculated as follows:

$$\lambda_U = \lambda_D \cdot F_\Psi$$

The values for  $F_\Psi$  are given in Table 6.

Table 9: Moisture conversion factor  $F_{\psi}$  derived from [4].

Level according to EN 13163	Practical water content $W_p$ vol-%		Moisture conversion factor $F_{\psi}$ 1	
	Drained	Not drained	Drained	Not drained
WL(T)5	$\leq 2,5$	$\leq 5,0$	1,11	1,22
WL(T)3	$\leq 1,5$	$\leq 3,0$	1,06	1,13
WL(T)2	$\leq 1,0$	$\leq 2,0$	1,04	1,08
WL(T)1	$\leq 0,5$	$\leq 1,0$	1,02	1,04

For the behaviour under water exposure in practical conditions see Table 9.

### 3.22 Long term water absorption by immersion

For some applications the long term water absorption is required. This can be measured for partial or total immersion. Both possibilities are described in EN 12087.

### 3.23 Long term water absorption by diffusion

For some applications (see 43) long term water absorption by diffusion must be declared. This shall be determined in accordance with EN 12088. The long-term water absorption by diffusion is not only used as an accelerated test but can also be used for classification.

### 3.24 Freeze thaw resistance

The determination of the freeze-thaw resistance is only needed for applications where EPS is permanently exposed directly to water and a temperature range from below zero up to higher than 0 °C. These conditions can occur in non-protected frost insulation systems (no gravel layers or insulation under groundwater etc.) or in inverted roofs.

The freeze-thaw resistance is tested according to EN 12091 in which the changes of compression strength and moisture content will be determined. The test has 300 cycles from dry conditions at the temperature of – 20 °C to the wet conditions at the temperature of + 20 °C. A large amount of measurements of the freeze-thaw resistance shows that EPS products having a density higher than 20 [kg/m³] and a bending strength of at least 150 [kPa] are not degraded by freeze-thaw cycles. Also the thermal conductivity of EPS frost insulation boards is not affected by freeze-thaw cycles.

The Canadian Institute for Research in Construction has tested moulded EPS boards in a perimeter application over a long term period of two years [38]. The thickness of boards was 76 mm and the density varied approximately from 12 to 18 [kg/m³]. After a two year monitoring period the measurements indicated stable thermal performance of EPS frost insulation. The thermal performance of the specimen was not significantly affected by water movement. It also appears that the EPS insulation protected the concrete during these events. Thermal conductivity showed no significant difference from that measured on the initial EPS product. Also the compressive strength of the EPS samples were the same as those of samples tested at the beginning of the test. The in situ performance of EPS frost insulation indicated a high stability of EPS.

For horizontal frost insulation materials, the determination of the freeze-thaw resistance is not necessary when the insulation is used in normal drained conditions (insulation above the ground water level). The ground slab should be surrounded from both sides by layers of gravel and sand that have low capillarity. These layers form a part of drainage system that keeps the free water level mainly below the insulation layer. EPS frost insulation should have only occasional contact with free water. At least a 200 [mm] layer of gravel and sand is recommended to be used between the free water level and frost insulation. The EPS frost insulation should also be protected against high moisture loads from above. Both the ground surface and the frost insulation layers should be inclined (at least 2 %) away from the building so that the possible free water from above will be lead away from the foundation. In the above mentioned conditions the long term moisture content of EPS frost insulation with properly arranged drainage of free water will typically be in the range of 0,5 to 2,5 % vol. [47].

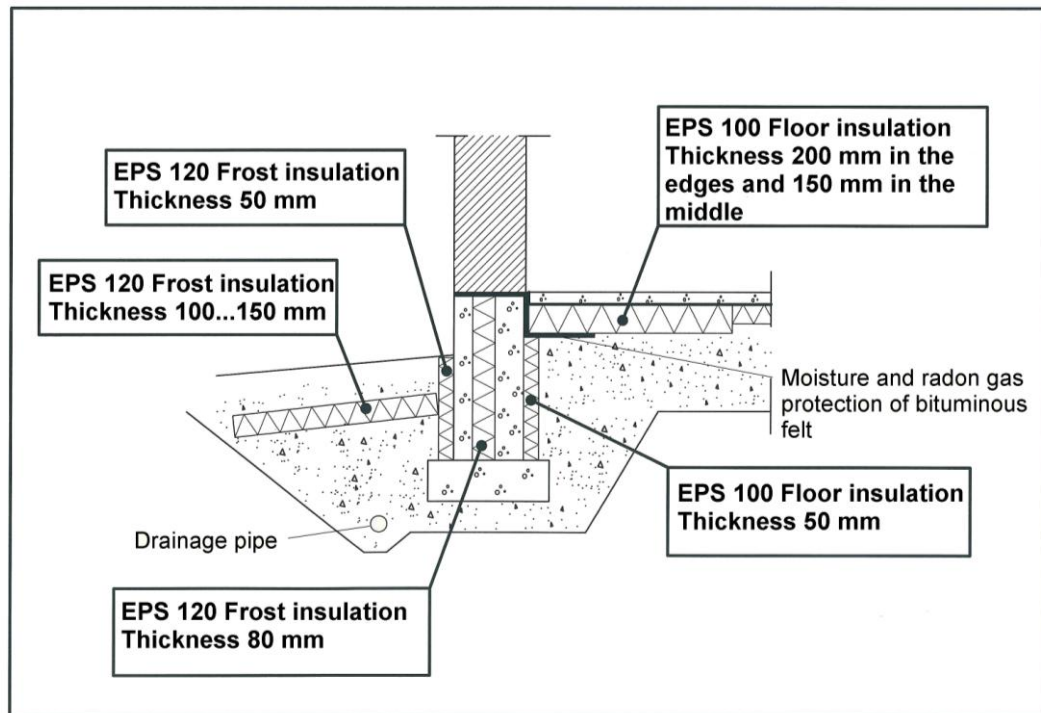


Figure 16:  
Example of how to use EPS frost and floor insulation materials in ground slab structures.

#### Conclusion:

- EPS frost insulation materials with a density of 22 [kg/m<sup>3</sup>] or above have good results in freeze-thaw tests, if the boards are well fused.
- The classification of Finnish EPS Division's EPS frost products is (based on test method EN 12087, method 2A):

EPS 120 Frost: short-term compressive strength at 10 % deformation 120 [kPa], and the moisture content below 2 vol %

EPS 200 Frost: short-term compressive strength at 10 % deformation 200 [kPa] and the moisture content below 1 vol %

EPS 300 Frost: short-term compressive strength at 10 % deformation 300 [kPa] and the moisture content below 1 vol %

EPS 400 Frost: short-term compressive strength at 10 % deformation 400 [kPa] and the moisture content below 1 vol %

### 3.25 Water vapour transmission

The water vapour transmission through the thermal insulation product is needed for constructions where the water vapour condensation has to be calculated. A calculation method for this purpose is given in EN 13788 [23], which defines water vapour diffusion resistance factors. These factors are given in Annex D, table D.2 of EN 13163. Since there is always a range given in table D.2 some national application rules require the use of the unfavourable value and therefore it has to be decided whether the upper or the lower value should be used. In cases where the condensation point is located inside the insulation layer the higher value should be used. In cases where the condensation point is located outside the insulation the lower value should be used. If the condensation is located inside the EPS layer it makes no difference which value has been chosen.

In addition to EN 12086, EN ISO 12572 is another test standard for this property. For other building materials EN 12524 [16] containing tabulated values may be used.

### **3.26 Water vapour diffusion resistance factor**

The water vapour diffusion resistance factor is used to calculate water vapour condensation inside a construction. For more details see

[Table 10: Tabulated values of water vapour diffusion resistance factors and water vapour permeability.](#)

In EN 12086 the following definitions are to be found:

Water vapour permeability,  $\delta$ :

The product of the permeance and the thickness of the test specimen. The water vapour permeability of a homogeneous product is a property of the material. It is the quantity of water transmitted per unit of time through a unit of area of the product per unit of vapour pressure difference between its faces for a unit thickness.

Water vapour diffusion resistance factor,  $\mu$ :

The quotient of the water vapour permeability of air and the water vapour permeability of the material or the homogeneous product concerned. It indicates the relative magnitude of the water vapour resistance of the product and that of an equally thick layer of stationary air at the same temperature.

The water vapour diffusion resistance factor  $\mu$  is normally given at a temperature of 20 °C and a barometric pressure of 1.011 [hPa]. The water vapour permeability,  $\delta_{air}$ , of air at that condition is:

$$\delta_{air} = \frac{D}{R_D \cdot T} \left( \frac{T}{273K} \right)^{1,81}$$

where

$$D = 0,083 \text{ [m}^2/\text{h]}$$

$$R_D = 462 \cdot 10^{-6} \text{ [Nm/(mgK)]}$$

$$\delta_{air} = \frac{0,083 \text{ m}^2/\text{h}}{462 \cdot 10^{-6} \text{ Nm/(mgK)} \cdot 283K} \left( \frac{283K}{273K} \right)^{1,81} = 0,635 \text{ mg/(Pa} \cdot \text{h} \cdot \text{m)} \cdot 0,965^{1,81} = 0,6 \text{ mg/(Pa} \cdot \text{h} \cdot \text{m)}$$

$$\delta = \frac{\delta_{air}}{\mu} = \frac{0,6}{\mu}$$

Due to this calculation table D.2 in EN 13163 has to be slightly revised as given in

[Table](#) 10.

Table 10: Tabulated values of water vapour diffusion resistance factors and water vapour permeability.

Type	Water vapour diffusion resistance factor $\mu_1$	Water vapour permeability $\delta$ mg/(Pa·h·m)
EPS 30	20 to 40	0,015 to 0,030
EPS 50	20 to 40	0,015 to 0,030
EPS 60	20 to 40	0,015 to 0,030
EPS 70	20 to 40	0,015 to 0,030
EPS 80	20 to 40	0,015 to 0,030
EPS 90	30 to 70	0,009 to 0,020
EPS 100	30 to 70	0,009 to 0,020
EPS 120	30 to 70	0,009 to 0,020
EPS 150	30 to 70	0,009 to 0,020
EPS 200	40 to 100	0,006 to 0,015
EPS 250	40 to 100	0,006 to 0,015
EPS 300	40 to 100	0,006 to 0,015
EPS 350	40 to 100	0,006 to 0,015
EPS 400	40 to 100	0,006 to 0,015
EPS 500	40 to 100	0,006 to 0,015
EPS T, EPS SD	20 to 40	0,015 to 0,030

### 3.27 Liquid water permeability of the system surface

Listed in EN 13499 only. Liquid water permeability shall be determined in accordance with EN 1062-3. No test result shall be greater than 0,5 [kg/(m<sup>2</sup>·h<sup>0.5</sup>)]. If the base coat complies with this requirement the finishing material need not be tested.

### 3.28 Characteristics for floating floors are listed in 3.27 and 3.28

When EPS is used in floating floors, characteristics must be determined according to different test methods compared to determination of other EPS characteristics.

### 3.29 Dynamic stiffness

The dynamic stiffness is needed for applications where acoustical performances have to be assessed. The type of EPS for this application is EPS T. The dynamic stiffness describes the transmission of vibrations through EPS between two layers. Low values of dynamic stiffness lead to a high sound reduction index

For indirect testing of dynamic stiffness see Annex B, clause B.2.5 of EN 13163. Normally the dynamic stiffness is needed to calculate the weighted impact sound reduction index of intermediate floors with a floating floor finish.

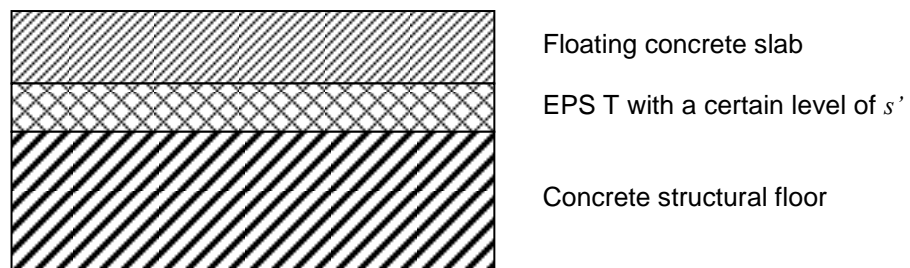




Figure 17: Example of a ceiling construction with a floating floor.

For detailed information how to calculate the impact sound reduction see the following example and EN 12354-2 [24].

#### Example

Two floors of a building are separated by an in-situ concrete solid floor, thickness 200 mm. To achieve a certain acoustic performance a floating floor, thickness 60 mm, made of concrete shall be fabricated on a layer of EPS T. The properties of the EPS T are:

thickness	40 [mm]
compressibility	3 [mm]
dynamic stiffness	10 [MN/m <sup>3</sup> ]

If the density of the concrete floor is 2.300 [kg/m<sup>3</sup>] and the density of the slab is 2.000 [kg/m<sup>3</sup>] the mass per unit area is

for the floor	460 [kg/m <sup>2</sup> ]
for the screed	120 [kg/m <sup>2</sup> ]

According to Annex B of EN 12354-2, equation B.5 the equivalent weighted normalised sound pressure level  $L_{n,w,eq}$  of homogeneous floor constructions is

$$L_{n,w,eq} = 164 - 35 \lg \frac{m'}{m'_0} \text{ [dB]}$$

where

$m'$  is the mass per unit area of the floor and  
 $m'_0$  is 1 [kg/m]

$$L_{n,w,eq} = 164 - 35 \lg \frac{460 \text{ kg/m}^2}{1 \text{ kg/m}^2} = 164 - 35 \lg 460 = 164 - 35 \cdot 2,663 = 70,8 \text{ dB}$$

The weighted reduction of impact sound pressure level,  $\Delta L_w$ , for floating floor screeds may be taken from figure C.1 of EN 12354-2. For a mass per unit area of the screed of 120 [kg/m<sup>2</sup>] and a dynamic stiffness of 10 [MN/m<sup>3</sup>] of the impact sound insulation layer  $\Delta L_w$  is 33 [dB].

The correction  $K$  for flanking transmission has to be taken from Table C.1 of EN 12354-2. Assuming the mean mass per unit area of the homogeneous flanking elements is 200 [kg/m<sup>2</sup>] the correction  $K$  will be 2 [dB].

Now the weighted normalized impact sound pressure level,  $L'_{n,w}$ , between two rooms can be calculated:

$$L'_{n,w} = L_{n,w,eq} - \Delta L_w + K = 71 \text{ [dB]} - 33 \text{ [dB]} + 2 \text{ [dB]} = 40 \text{ [dB]}$$

Normally this is the required value in national application rules. If the weighted standardized impact sound pressure level is required the volume,  $V$ , of the receiving room has to be taken into account. Assuming a volume of 50 [m<sup>3</sup>]:

$$L'_{nT,w} = L'_{n,w} - 10 \lg(V/30) = 40 \text{ [dB]} - 2,2 \text{ [dB]} = 38 \text{ [dB]}$$

Furthermore products having a low value of dynamic stiffness improve the performance concerning air born sound in some constructions like gypsum board faced walls or ETICS. For this application a method is being developed to measure the air born sound insulation. A draft is being set up in TC 88 WG 18.

The following equation can be used:

$$R'_{w,R} = R'_{w,R,O} + \Delta R'_{w,R} \text{ [dB]}$$

where

$R'_{w,R}$  = Air born sound insulation of an ETICS wall

$R'_{w,R,O}$  = Air born sound insulation of the carrier wall

$\Delta R'_{w,R}$  = Correction value, using the following equation:

$$\Delta R'_{w,R} = \Delta R'_w - K_K - K_T \text{ [dB]}$$

where

$\Delta R'_w$  = Correction value depending on the resonance frequency (see Table 11)

$K_K$  = Correction for the percentage adhesive surface (see Table 12)

$K_T$  = Correction for the evaluated sound insulation level of the carrier wall (see Table 13)

Table 11: Correction value depending on the resonance frequency

Resonance frequency $f_R$ [Hz]	Correction value $\Delta R_w$ [dB]	
	Without dowels	With dowels
$f_R \leq 60$	13	7
$60 < f_R \leq 70$	12	6
$70 < f_R \leq 80$	10	5
$80 < f_R \leq 90$	8	4
$90 < f_R \leq 100$	6	2
$100 < f_R \leq 120$	4	1
$120 < f_R \leq 140$	2	-1
$140 < f_R \leq 160$	0	-2
$160 < f_R \leq 180$	-1	-3
$180 < f_R \leq 200$	-3	-4
$200 < f_R \leq 220$	-4	-4
$220 < f_R \leq 240$	-5	-5
$240 < f_R$	-6	-6

The resonance frequency,  $f_R$ , is to be calculated from the level of the declared dynamic stiffness in accordance with clause 4.3.12 of EN 13163:

$$f_R = 160 \sqrt{s' / m'_p}$$

where

$f_R$  = resonance frequency [Hz]

$s'$  = the dynamic stiffness of the EPS board [MN/m<sup>3</sup>]

$m'_p$  = area mass of the plaster layer [kg/m<sup>2</sup>]

Table 12: Correction for the percentage adhesive surface

Percentage adhesive surface (%)	$K_K$ [dB]
20	-1
40	0
60	1
80	2
100	3

Table 13: Correction for the evaluated sound insulation level of the carrier wall

Resonance frequency $f_R$ [Hz]	$K_T$ [dB] depending on the evaluated sound insulation level of the carrier wall $R_w$ [dB]					
	43-45	46-48	49-51	52-54	55-57	58-60

$f_R \leq 60$	-10	-7	-3	0	3	7
$60 < f_R \leq 80$	-9	-6	-3	0	3	6
$80 < f_R \leq 100$	-8	-5	-3	0	3	5
$100 < f_R \leq 140$	-6	-4	-2	0	2	4
$140 < f_R \leq 200$	-4	-3	-1	0	1	3
$200 < f_R \leq 300$	-2	-1	-1	0	1	1
$300 < f_R \leq 400$	0	0	0	0	0	0
$400 < f_R \leq 500$	1	1	0	0	0	-1
$500 < f_R$	2	1	1	0	-1	-1

Calculation of the sound insulation level,  $R_W$ , of the carrier wall shall be calculated as:

$$R_W = (27,1 + 0,1243(m'_W - m'_0) - 0,000113(m'_W - m'_0)^2) \text{ [dB]}$$

where

$R_W$  = sound insulation level [dB]

$m'_W$  = area-based mass of the carrier wall [kg/m<sup>2</sup>]

$m'_0$  = normative mass [kg/m<sup>2</sup>]

### 3.30 Compressibility

The compressibility is used for EPS T products applied in load bearing constructions like floating floors. Since there are different levels of imposed load on the screed the compressibility levels are given in correlation to those load levels. To determine the compressibility,  $c$ , the thickness  $d_L$  and the thickness  $d_B$  have to be measured first.

$$c = d_L - d_B$$

For constructions with a level of imposed load up to 5 kPa there is a great deal of experience of the long term behaviour. In these cases the long term thickness reduction is lower than or equal to  $c$  if the requirements of table 12 of EN 13163 are met. For higher levels of imposed load the long term thickness reduction,  $X_t$  must be determined in accordance with EN 1606.

### 3.31 Apparent density

The apparent density is not a product performance but a very important parameter for quality assessment and for indirect testing. Many of the properties of an EPS product relate to density such as thermal conductivity, bending strength, deformation under load, compressive stress, tensile strength, compressive creep, water absorption, freeze thaw resistance, water vapour transmission, dynamic stiffness, compressibility, shear strength, dynamic load resistance. The properties bending strength, tensile strength, water absorption, freeze thaw resistance, water vapour transmission and shear strength depend very much on the fusion of the material. Guidance on how to use the density for indirect testing is given in the Annex B, clause B.2 of EN 13163.

### 3.32 Release of dangerous substances

#### 3.32.1 General

The European Community has decided already in the CPD in 1990 that construction products should not emit or leach "dangerous" substances to the environment or should not contain "substances of very high concern". Guidance Paper H [29] is considered as the basic reference document with regard to the definition (and consequently the scope) and the approach 'dangerous substances' within the framework of the CPD.

The definition of 'dangerous substances' derived from the Guidance Paper and the CPD is:

- based on the release approach,
- focussed on the intended application of construction products,
- restricted to the normal use of construction products.

CEN has been requested to develop procedures and test methods of for the relevant release scenarios (emissions into indoor air, release into soil, ground water and surface water, radiation etc.) by the EC Mandate M 366.

A list of relevant dangerous substances released from construction products to the different types of environment to be protected when applied in the works was needed and taken from the existing DG Enterprise G5 database [30].

Some documents were already published by CEN TC 351:

- CEN/TR 16220 Construction products. Assessment of release of dangerous substances. Complement to sampling
- CEN/TS 16516 Construction products - Assessment of release of dangerous substances - Determination of emissions into indoor air
- CEN/TR 16496 Construction Products - Assessment of release of dangerous substances

Use of harmonised horizontal assessment methods CEN TC 351 has - fall 2010 - drafted two sets of procedures to determine the release of these "Regulated Dangerous Substances (RDS)" and the EC funded TC 351 with budget for ruggedness testing of these procedures. Until verification of the procedures, the draft testing methods will not be available for use by involved parties (e.g. authorities, experts, institutes, contractors, producers).

On request of DG Enterprise EUMEPS has submitted a draft proposal –as part of CEN TC 88\_ to prove that EPS fulfils all the requirements on release and emissions Europe wide.

### **3.32.2 Specific to EPS**

EPS does not release any of the dangerous substances listed in reference [30] in such a way that it does not fulfil the local European environmental laws and guidelines. The released concentrations are of a lower order than the values set out in these legislations.

### **3.33 Continuous glowing combustion**

For the time being this clause is placed in the standard as a placeholder. An EN test method is currently under development.

**Characteristics specific for building equipment and industrial installations are listed in 3.33 to 3.35**

### **3.34 Maximum service temperature**

The maximum service temperature must be determined when a product is applied at high temperatures. For EPS the commonly used maximum service temperature is 80 °C (over 80 °C EPS will start to shrink). Measuring the maximum service temperature is therefore not necessary, only when EPS specialties (co-polymers of EPS) are used.

### **3.35 Minimum service temperature**

The minimum service temperature must be determined when a product is applied at low temperatures. No harmonised EN test method is developed, because apparently different insulation materials react different on low temperatures. To determine the minimum service temperature a test method that is applicable for plastic insulation materials is put in the standards for plastic insulation materials in an Annex, explaining the way to test the thermal conductivity and dimensions before and after the test..

### 3.36 Trace quantities of water soluble ions and pH


In certain applications a limit can be put to trace quantities of water soluble chloride, fluoride, silicate and sodium ions. A test method to determine those quantities and measuring the pH is developed (EN 13468).

The additional characteristics listed in 3.36 to 3.45 do not appear in the standards, but are useful.

### 3.37 Correlation between bending and tensile strength

The following correlation between bending strength and tensile strength was measured FIW.

Figure 18: Correlation between bending and tensile strength.

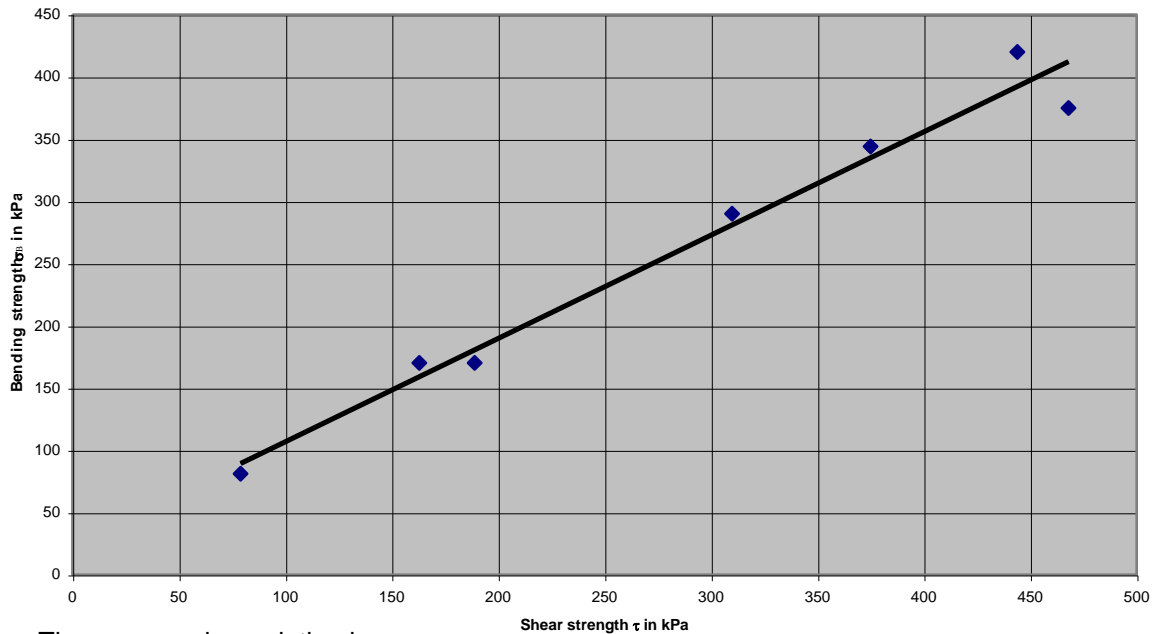

The measured correlation is

$$\sigma_b = 0,83\tau + 23,6 \text{ [kPa]}$$

### 3.38 Moisture content

The moisture content should be determined in accordance with EN 12570 [14]. In cases where EPS is installed between layers of other materials assessment according to EN ISO 12571 [15] may be useful.

### 3.39 Thermal expansion

The thermal expansion is used to calculate the reversible change of the dimensions versus the temperature.

$$x_{th} = x(1 + \alpha_{th} \cdot \Delta T)$$

Where  $\alpha_{th}$  is the material specific coefficient of thermal expansion. The coefficient of thermal expansion was measured by Zehendner [21] and is indicated

Table 14.

Table 14: Coefficients of thermal expansion of EPS.

Material	Density [kg/m <sup>3</sup> ]	Direction in respect on the board	Coefficient [K <sup>-1</sup> ]
EPS Block moulded Non flame retarded	14	parallel	$9,3 \cdot 10^{-5}$
		perpendicular	$8,0 \cdot 10^{-5}$
	23	parallel	$6,7 \cdot 10^{-5}$
		perpendicular	$6,7 \cdot 10^{-5}$
EPS Block moulded flame retarded	13	parallel	$9,5 \cdot 10^{-5}$
		perpendicular	$9,8 \cdot 10^{-5}$
	20	parallel	$7,2 \cdot 10^{-5}$
		perpendicular	$7,8 \cdot 10^{-5}$
EPS moulded board	42	parallel	$6,4 \cdot 10^{-5}$
		perpendicular	$6,7 \cdot 10^{-5}$

### 3.40 Hygric expansion coefficient

EPS products have no essential hygric expansion. In cases where this property (e. g. for coatings and facings) is needed it should be determined in accordance with EN 13009 [13].

### 3.41 Specific heat capacity

Tabulated values of the specific heat capacity of most building products are to be found in EN 12524 [16]. The specific heat capacity,  $c_p$ , of polystyrene is 1.300 [J/(kg·K)]. The energy,  $Q$ , which is taken up or given up by polystyrene at a change of the temperature,  $\Delta T$ , is calculated:

$$Q = m \cdot \Delta T \cdot c_p \quad [\text{J}]$$

where  $m$  is the mass of polystyrene.

### 3.42 Chemical resistance

The resistance of EPS to chemicals depends partly on the way of manufacturing. The surface area of boards cut from a block gives a larger opportunity for chemical to penetrate than the surface area of moulded products. Also a lower density is damaged more rapidly than higher densities.

In practice (e. g. in the construction or packaging sectors) it is very important to know how EPS reacts to chemical substances in order to prevent faults in application.

The test for resistance is based on [40] "Testing of expanded foam materials; Determination of the reaction to liquids, vapours, gases and solid materials". In this DIN standard, 5 foam cubes without expansion skin and with sides measuring 5 [cm] are immersed in the test medium for a definite length of time and changes occurring in the samples, e.g. in mass and dimensions, are determined. The exposure time depends on the test medium: for liquids it is 72 hours; for gases 24 hours and for liquefied gases, at least three hours.

For liquefied gases the immersion temperature is at, or just under, the boiling point of the test medium in question; in other media, immersion takes place at room temperature.

For visual assessment of damage, DIN 53428 suggests a scale of criteria from 0 (no change) to 5 (severely damaged). To provide a simplified overview, *Table 15* contains the following assessment criteria:

+	= unchanged ( $\geq 0$ )	= resistant
+-	= slight change ( $\geq 2$ )	= limited resistance (small change in dimensions)
-	= severely damaged ( $\geq 5$ )	= not resistant

If EPS comes into contact with substances of unknown composition that could contain damaging solvents (e.g. paints or adhesives) it should be ensured in advance that the foam is not attacked by carrying out a trial under field conditions. The trial may be shortened considerably if it is carried out at temperatures above 20 °C (e.g. 50 °C). To obtain clearer evidence of the foam's resistance, the severity of the test conditions can be increased by testing foam with a density is much lower than that intended for the intended application.

Table 15 shows the resistance of expanded foam to the most important chemical substances.

Table 15: Chemical behaviour of EPS, derived from [3].

Water:		Gases:		Alcohols:	
Sea water	+	a) inorganic		Methanol	+-
Water	+	Ammonia	-	Ethanol	+-
		Bromine	-	Ethylene glycol	+
<b>Alkalis:</b>		Chlorine	-	Diethylene glycol	+
Ammonia water	+	Sulphur dioxide	-	Isopropanol	+
Bleaching solutions (hypochlorite, Hydrogen peroxide)	+			Butanol	+-
Potassium hydroxide solution	+	b) organic		Cyclohexanol	+
Lime water	+	Butadiene	-	Glycerine	+
Caustic soda solution	+	Butane	-	Coconut oil alcohol	+
Soap solutions	+	Butene	-		
		Natural gas	+	<b>Amines:</b>	
		Ethane	+	Aniline	-
<b>Dilute acids:</b>		Ethene (ethylene)	+	Diethylamine	-
Formic acid, 50%	+	Ethyne (acetylene)	+	Ethylamine	+
Acetic acid, 50%	+	Methane	+	Triethylamine	-
Hydrofluoric acid, 4%	+	Propane	+		
Hydrofluoric acid, 40 %	+	Propene (propylene)	+	<b>Miscellaneous organic substances:</b>	
Phosphoric acid, 7 %	+	Propene (propylen) oxide	-	Acetone	-
Phosphoric acid, 50%	+			Acetonitrile	-
Nitric acid, 13 %	+	<b>Liquefied gases:</b>		Acrylonitrile	-
Nitric acid, 50%	+	a) inorganic		Dimethylformamide	-
Hydrochloric acid, 7%	+	Ammonia	+	Esters	-
Hydrochloric acid, 18 %	+	Inert gases	+	Ethers	-
Sulphuric acid, 10%	+	Oxygen (risk of explosion)	+	Halogenated hydrocarbons	-
Sulphuric acid, 50%	+	Sulfur dioxide	-	Ketones	-
		Nitrogen	+	Paint thinners	-
		Hydrogen	+	Olive oil	+
<b>Concentrated acids:</b>				Tetrahydrofuran	-
Formic acid, 99 %	+	b) organic			
Acetic acid, 96 %	-	Methane	+	<b>Inorganic building materials:</b>	
Propane acid, 99%	-	Ethane	+	Anhydrite	+
Nitric acid, 65 %	+	Ethene	-	Gypsum	+
Hydrochloric acid, 36 %	+	Ethene oxide	-	Lime	+
Sulphuric acid, 98 %	+	Ethyne (acetylene)	-	Sand	+
		Propane	-	Cement	+
		Propene	-		
<b>Fuming acids:</b>		Propene oxide	-	<b>Organic building materials:</b>	
Nitric acid	-	Butane	-	Bitumen	+
Sulphuric acid	-	Butene	-	Water-based rapid-curing cutback and bituminous knife fillers	+
		Butadiene	-	Solvent-based rapid-curing cutback and bituminous knife fillers (free from aromatics)	-
		Natural gas	+		
<b>Anhydrides:</b>				<b>Aromatics:</b>	
Acetic anhydride	-			Benzene	-
Carbon dioxide, solid	+	<b>Aliphatic hydrocarbons:</b>		Cumene	-
Sulphur trioxide	-	Cyclohexane	-	Ethylbenzene	-
		Diesel fuel, Heating oil	-	Phenol, 1 % aqu. soln.	+
		Heptane	-	Phenol, 33% aqu. soln.	-
<b>Weak acids:</b>		Hexane	-	Styrene	-
Humic acid	+	Paraffin oil	+-	Toluene	-
Carbonic acid	+	White spirit 55-95 °C	-	Xylene	-
Lactic acid	+	White spirit 155-185 °C	-		
Tartaric acid	+	Vaseline	+	<b>Vapors of:</b>	
Citric acid	+	Gasoline (regular & super grades)	-	Camphor	-
				Naphthalene	-



Specific raw materials of polystyrene can be used to produce EPS that have increased resistance to aromatic free hydrocarbons by comparison with other EPS grades. The suitability of products for a particular application must be checked in each case. The information submitted in this publication is based on current knowledge and experience. In view of the many factors that may affect processing and application, these data do not relieve processors of the responsibility of carrying out their own tests and experiments; neither do they imply any legally binding assurance of certain properties or of suitability for a specific purpose.

### **3.43 Air permeability**

The air permeability of EPS in normal use is not needed. If in special cases this property is required it can be measured according EN 12114 [12].

### **3.44 Electrical properties**

The electrical characteristics are similar to those of air. The dielectrical constant of EPS has a value of 1 in the frequency range from 100 [Hz] to 1 [GHz] at a temperature of 25 °C. The surface resistance is  $10^{11}$  to  $10^{13}$  [Ohm] at a relative humidity of 50 %.

### **3.45 Sustainability, LCA data and EPD's**

Based on growing concern for the environment, and in particular an increasing demand for sustainable building and development, the EC has commissioned CEN to develop horizontal standards regarding the sustainability of construction works. CEN TC 350 was established.

The following documents were already published by CEN TC 350:

- EN 15643-1 Sustainability of construction works - Sustainability assessment of buildings - General framework
- EN 15643-2 Sustainability of construction works - Assessment of buildings -Framework for the assessment of environmental performance
- EN 15643-3 Sustainability of construction works - Assessment of buildings - Framework for the assessment of social performance
- EN 15643-4 Sustainability of construction works. Assessment of buildings. Framework for the assessment of economic performance
- EN 15804+A1 Sustainability of construction works - Environmental product declarations - Core rules for the product category of construction products
- EN 15978 Sustainability of construction works - Assessment of environmental performance of buildings - Calculation method.

EN 15804 + A1 provides core product category rules (PCR) for Type III environmental declarations for any construction product and construction service. It provides a structure to ensure that all Environmental Product Declarations (EPD) of construction products, construction services and construction processes are derived, verified and presented in a harmonised way. EPD provide the data to assess the sustainability of construction works.

EUMEPS already carried out in 1998 a study fulfilling the requirements of the international ISO 14040 standard [45], [46], [47]; reflecting the best available LCA data on EPS that could be made available. They can be found in the [EUMEPS brochure](#) on page 26.

## 4 Application and calculation

### 4.1 Eurocodes calculation rules for EPS

#### 4.1.1 Introduction

In this clause the calculation rules of expanded polystyrene (EPS) are given for EPS in geotechnical/ civil engineering applications [57].

#### 4.1.2 Design rules

A lot of nonofficial, voluntary design rules in the EU are used (e.g. FGSV, CROW and NRRL guidelines). With Eurocodes into force designers and engineers are bound to fundamental approaches, as agreed within CEN. Design rules were voluntary; now the Eurocodes are mandatory and legal. This clause describes general rules as a help to design the required EPS properties.

#### 4.1.3 Loadings

Loadings of own weight and imposed dead loads can be derived from Eurocodes; for EPS a design value of 50 [kg/m<sup>3</sup>] is mostly taken into account, independent of the dry mass but eventual water uptake included. The higher the density, the lower the water uptake, thus resulting in the average of 50 [kg/m<sup>3</sup>]. For traffic (cyclic) loads idem from Eurocodes.

#### 4.1.4 Loading factors

For safety class RC1 (the most used class) permanent loads a loading factor of  $\gamma_{F;G} = 1,08$  has to be applied; for traffic load a loading factor of  $\gamma_{F;Q} = 1,35$  (EN 1997 Annex A3 Table A3, collection A1 with a reduction of 0,9) has to be applied.

For safety class RC2 permanent loads a loading factor of  $\gamma_{F;G} = 1,2$  has to be applied; for traffic load a loading factor of  $\gamma_{F;Q} = 1,5$ .

In case of a possibility of floating other factors have to be used; for favourable loads is a factor of 0,9 valid; see EN 1997-1.

## 5 Design criteria

- *Ultimate Limit state (STR) short term* Loading combination: Multiply the dead and imposed load with their respective loading factors and compare it with the short term design compressive strength  $\sigma_{10;d}$  (e.g. 90,9 kPa for EPS 100).
- *Ultimate Limit state (STR) permanent* Loading combination: Multiply the dead load and the permanent part of the imposed load (mostly 0 in civil applications) with their respective loading factors and compare it with the long term design strength  $\sigma_{10;perm;d}$  (e.g. 27,3 [kPa] for EPS 100).
- *Ultimate Limit state (GEO) cyclic loads* Loading: Multiply the cyclic load with the factor  $\gamma_Q = 1,35$  (in case of RC1) and compare it with the design cyclic strength  $\sigma_{10;cycl;d}$  (e.g. 31,8 [kPa] for EPS 100).
- *Ultimate Limit state (UPL) floating* See Annex A4 of Eurocode 7; load factor  $\gamma_{G;stb} = 0,9$  in favourable situation and  $\gamma_{G;dst} = 1,0$  in unfavourable situation for permanent actions. Load factor  $\gamma_{Q;dst} = 1,5$  in unfavourable situation for variable actions.
- *Construction phase* The worst case scenario to be taken, taking into account a missing pressure equalising layer.

### Example 1: Calculation typical Dutch polder road


As an example a typical road in the “Polders” in the western part of the Netherlands is taken.

Construction:

Depth (removing peat soil): 1,4 [m]; Highest groundwater level 40 [cm] under ground level: applied EPS 100 blocks 2 [m] high; 0,5 [m] sand/gravel; 0,15 [m] asphalt.

Safety class RC1

Hardeningscalculation shows a variable/cyclic loading of 15 [kPa] imposed on the EPS.

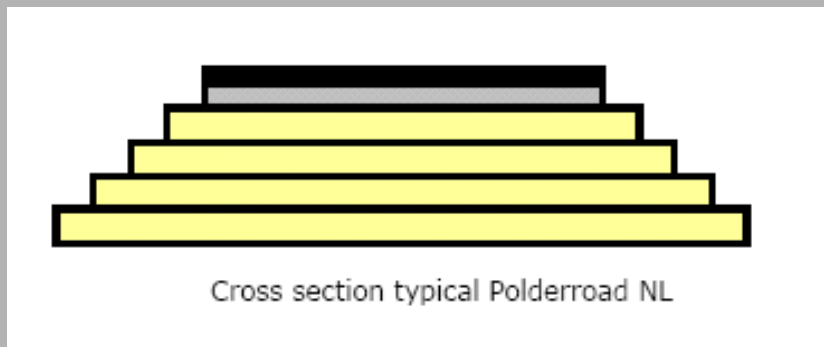

Loadings:

*Permanent loads* ( $\gamma=1,08$ )

0,15 [m] asphalt bitumen layers	$0,15 * 2100 \text{ [kg/m}^3\text{]} = 3,1 \text{ [kN/m}^2\text{]}$
0,50 [m] gravel/sand	$0,50 * 1800 \text{ [kg/m}^3\text{]} = 9,0 \text{ [kN/m}^2\text{]}$
2,00 m EPS 100	$2,00 * 50 \text{ [kg/m}^3\text{]} = 1,0 \text{ [kN/m}^2\text{]}$
	<b>P = 13,1 [kN/m<sup>2</sup>]</b>

*Traffic load* ( $\gamma = 1,35$ )

Cyclic and uniformly distributed on EPS = 15,0 [kN/m<sup>2</sup>]

*Loading combinations:*


<i>STR- short:</i> $1,08 * 13,1 + 1,35 * 15$	$= 34,40 \text{ [kPa]} < 90,9 \text{ OK}$
<i>STR-permanent</i> $1,08 * 13,1$	$= 14,15 \text{ [kPa]} < 27,3 \text{ OK}$
<i>GEO-Cyclic</i> $1,35 * 15$	$= 20,25 \text{ [kPa]} < 31,8 \text{ OK}$
<i>Floating</i> $(1,4 - 0,4) * 1,1, * 10 - 0,9 * 13,1$	$= 11- 11,8 \text{ OK (just enough)}$

**Conclusion:** The product properties of EPS 100 fulfil the performance requirements. In this case even EPS 60 would have been sufficient, but for practical reasons EPS 100 was chosen.

Example 2: Calculation cycle barn in dwelling area

## Description

A cycle barn, dimensions 2,70 \* 3,20 [m]; height 2,40 [m]; single brick walls, timber roof structure, concrete floor 0,12 [m] thickness.

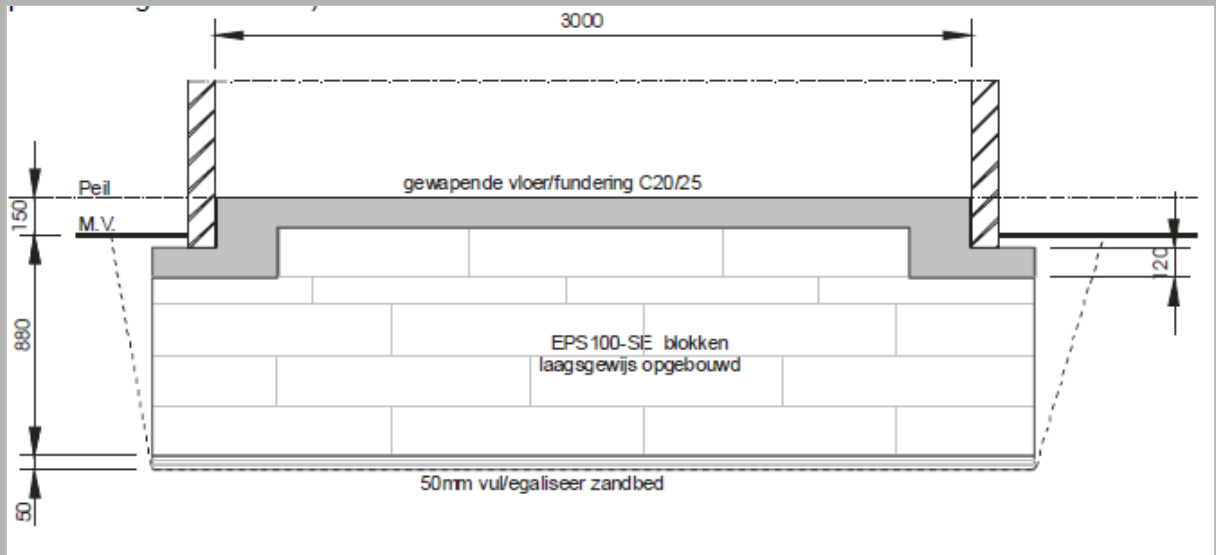

## Loadings:

The total weight has been calculated at :  $Q_{G,rep} = 108$  [kN]  
 Imposed load (live load):  $Q_{Q,rep} = 10$  [kN]  
 permanent part of live load:  $4$  [kN]

## Loading combinations:

*STR- short:*

$$1,08 * 108 + 1,35 * 10 = 130,4 \text{ [kN].}$$

*STR-permanent*

$$1,08 * 108 + 1,35 * 4 = 122,04 \text{ [kN]}$$

## Design values:

Applied is EPS100 with  $\sigma_{10;d} = 90,9$  [kPa] and  $\sigma_{10;perm;d} = 31,8$  [kPa]

Length of the foundation : 3,50 [m]; width: 3,0 [m]; surface: 10,50 [m<sup>2</sup>]

STR-short gives:  $130,4 / 10,50 = 12,41$  [kPa] < 90,9 OK

STR- long gives:  $122,04 / 10,50 = 11,62$  [kPa] < 31,8 OK

## Floating possible?

The max GWL is 0,15 [m] below upper side EPS; total floating force:  $0,73$  [m] \*  $10,50$  [m<sup>2</sup>] \*  $10$  [kN] is  $76,65$  [kN];  $\gamma_{float} = 1,1$  and  $\gamma_{dead load} = 0,9$  acc. to Eurocodes, so the safety factor is:  
 $108 * 0,9 / 76,65 * 1,1 = 1,15$  sufficient acc. to Dutch rules (1,1 in CROW 150 guideline)

### 5.1 *International Application standards*

EN 14114	Thermal insulation of building equipment and industrial installations – Calculation of water vapour diffusion – Cold pipe insulation systems
ISO/CD 12575-1	Building applications – Foundation insulating systems – Materials - Specification
ISO DTR 9774	Properties of thermal insulation products for buildings according to their application – Guideline for the harmonization of international standards or specifications
EN 13499	Thermal insulation products for buildings – External thermal insulation composite systems (ETICS) based on expanded polystyrene - Specification
UEATC Rules	

### 5.2 *European Calculation standards*

EN 832	Thermal performance of buildings – Calculation of energy use for heating – Residential building
EN 1190	Thermal performance of buildings – Heat exchange with the ground – Calculation methods
EN 1997	Eurocode 7, Geotechnical design
EN 13947	Thermal performance of curtain walling – Calculation of thermal transmittance – Simplified method
EN 27345	Thermal insulation – Physical quantities and definitions
EN 29251	Thermal insulation – Heat transfer conditions and properties of materials – Vocabulary
EN 29288	Thermal insulation – Heat transfer by radiation – Physical quantities and definitions
EN 29346	Thermal insulation – Mass transfer – Physical quantities and definitions
EN 30211	Building components and building elements – Thermal resistance and thermal transmittance – Calculation method
EN 32573	Thermal bridges in building construction – Heat flows and surface temperatures – General calculation methods
EN 33786	Thermal performance of building elements – Thermal inertia characteristics – Calculation methods
EN 33789	Thermal performance of buildings – Specific heat loss – Calculation method
EN ISO 10211-1	Thermal bridges in building constructions – Heat flows and surface temperatures – General calculation methods
EN ISO 10211-2	Thermal bridges in building construction – Calculation of heat flows and surface temperatures – Linear thermal bridges
EN ISO 13370	Thermal performance of buildings – heat transfer via the ground – Calculation methods
EN ISO 13786	Thermal performance of building components – Dynamic thermal characteristics – Calculation methods
EN ISO 13788	Hygrothermal performance of building components and building elements – Internal service temperature to avoid critical surface humidity and interstitial condensation - Calculation methods
EN ISO 13790	Thermal performance of buildings – Calculation of energy use for space heating
EN ISO 13791	Thermal performance of buildings – Internal temperatures in summer of a room without mechanical cooling – General criteria and calculation procedures
EN ISO 13792	Thermal performance of buildings – Internal temperatures in summer of a room without mechanical cooling – General criteria for simplified calculation methods
EN ISO 14683	Thermal bridges in building constructions – Linear thermal transmittance – Simplified method and defaults values
EN ISO 15927-1	Hygrothermal performance of buildings – Calculation and presentation of climatic data – Data for accessing the annual energy demand for cooling and heating systems
EN ISO 15927-4	Hygrothermal performance of buildings – Calculation and presentation of climatic data – Data for accessing the annual energy demand for cooling and heating systems

EN ISO 15927-5	Hygrothermal performance of buildings – Calculation and presentation of climatic data – Winter external design air temperatures and related wind data
EN ISO 6946	Building components and building elements – Thermal resistance and thermal transmittance – Calculation method
EN ISO 8497	Thermal insulation – Determination of steady-state thermal transmission properties of thermal insulation for circular pipes
EN ISO 9251	Thermal insulation – Heat transfer conditions and properties of materials - Vocabulary
EN ISO 9288	Thermal insulation – Heat transfer by radiation – Physical quantities and definitions
EN ISO 9346	Thermal insulation – Mass transfer – Physical quantities and definitions
ISO 13789	Thermal performance of buildings – Transmission heat loss coefficient – Calculation method

### 5.3 National Application rules

#### Austria

ÖN B 3806	Anforderungen an Baustoffe im Bauwesen in brandschutztechnischer Hinsicht
-----------	---

#### Germany

DIN V 4108-4	Wärmeschutz und Energieeinsparung in Gebäuden – Wärme- und feuchteschutztechnische Kennwerte
DIN V 4108-10	Wärmeschutz und Energieeinsparung in Gebäuden – Anwendungsbezogene Anforderungen an Wärmedämmstoffe – Werkmäßig hergestellte Wärmedämmstoffe
For CEA	Merkblatt für die Verwendung von EPS-Hartschaumstoffen beim Bau von Straßendämmen – Forschungsgesellschaft für Straßen- und Verkehrswesen

#### France

DTU 26.2/52.1	Travaux de bâtiment – Mise en oeuvre des sous couche isolantes sous chape ou dalle flottantes et sous carrelage (Building works – Placing of insulating underlayers underneath floating floor screeds or floors and underneath tile flooring)
---------------	--

#### Finland

For floor and frost insulation products requirements for water absorption by immersion are given. For wall and roof applications water vapour transmission properties are required. Certificates are provided by VTT.

#### Netherlands

The Building Regulations (Bouwbesluit). Performance requirements are based on the function of the use of the relevant construction-part. Per aspect a “tabulated building rule” is given.

For buildings as a whole performance on energy is defined as the EPC-value (energy performance coefficient) with minimum requirements for the k-value of insulation in floors, walls and roofs.

The EPC-value is dependent on: the insulation, ventilation and installation, the situation of the components towards the sun etc.

Producers are bringing naked EPS as commodities on the market to be applied guarded by concrete / brickwork or as insulated panels for gables, pitched and flat roofs.

For applications materials and products are brought on the market with voluntary quality assurance, KOMO-certified and to be accepted by local authorities as if expected to fulfil the requirements.

The requirements on reducing energy consumption are set in the “Building Regulations”, in terms of an energy performance factor (E.P.C.) for the total

building. Regardless of that threshold values are given for individual components, separating outdoor climate ( $k < 0,4$ ). Additional requirements are given for reducing air permeability of the building. Reaction to fire requirements are set in terms of performance requirements on the construction parts in end use applications. For the time being present NEN standards are considered on this.

### Slovakia

STN 72 722-1 Thermal insulation products for buildings. Part 1: Types of building structures and application codes

This standard specifies the types of building structures and codes which are used for thermal insulation products in building construction. This standard applies to thermal insulation products by standards STN EN 13162 to STN EN 13171.

The informative Annex A provides an overview of the performance of thermal insulation products of brand, units and reference of the regulations.

STN 72 722-2 Thermal insulation products for building applications. Part 2: Factory made products of expanded polystyrene (EPS). Intended use

This standard specifies the class or level of the feature that the product has achieved to demonstrate his fitness for the intended use, while respecting the basic requirements for construction works. Applies for the purposes of the design and building of works under special regulations for the usual types of structures and the use category.

This standard complements STN EN 13163.

This standard also applies to products used for sound insulation and determines the sound isolation characteristics which are evaluated according STN 73 0532

This standard also applies to products used in prefabricated thermal insulation systems and composite panels and includes performances of systems containing these products.

STN 73 2901 Performance of External thermal insulation composite systems (ETICS)

This standard specifies the technical requirements for the manufacture of external thermal insulation composite systems (ETICS) with thermal insulation based on expanded (foamed) polystyrene (EPS), mineral wool (MW) and appropriately based on other thermal insulation for example. phenolic foam (PF), polyurethane (PU) with a finished plaster or plaster with paint, bonded to the substrate using adhesive or adhesive and expansion anchors supplied by the manufacturer on the market as a complete system. ETICS provides primarily thermal protection of buildings and their protection against climatic influences. It does not ensure the airtightness of the thermal building structure, which is achieved by the construction works when making ETICS.

### Spain

Spain has no additional rules in the application field of EPS.

### Sweden

In Sweden there are:

BBR Building Rules, Byggregler 1999

and

Construction Rules BKR 1999

These rules are connected to guidelines or about 10 handbooks.

Energy saving and insulation requirements are given in 2 guidelines. They are connected to EN-ISO 6946, but will be revised and published in 2003.

The U-value has to be calculated of the whole building. The U-value shall not exceed the value:

$$U_{m, \text{krav}} = 0,18 + 0,95 \cdot A_f / A_{om}$$

where

$A_f$  is the total area of windows, doors, gates

$A_{om}$  is total perimetric area that has normal room temperature

$U_{m, krav}$  is the highest accepted average U value.

The average  $U_m$  value for the building is calculated as:

$$U_m = (\sum (U_i \cdot A_i)) / A_{om}$$

For these U value calculations the computer program EPSU is used and developed by the Swedish Plastic Federation. The program is free for designers.

## 5.4 European EPS Types

### 5.4.1 EUMEPS EPS types

The thermal insulation product standards form a list of requirements of which the properties have to be declared by the manufacturer. These requirements are given in levels or classes to comfort all parties involved in comparing the specifications offered by the manufacturer on the one hand and the customer or legislator on the other hand. Two series of requirements exist: for general applications and for specific applications. National or local Building Regulation requirements are set for products in end use-conditions and not to materials as such placed on the market. The EPS product standard (EN 13163) is a so called "open standard". It gives the producer the possibility to define his own product specifications and declare them to the market. This freedom enables him to offer products with an optional performance, a specified use of recycle material and specific production methods. There is no reference to density: density can, through a known relationship, be used for internal quality control, when for indirect testing a reference to a specific property is known.

An example: EPS that is used in sandwich panels is subject to shear forces but the market requires a minimal thickness e.g. lambda value. Other examples lay in the field of frost and perimeter insulation. Manufacturers of EPS offering/producing "downstream" products to the market will develop their own specific product types. Bringing EPS to the market for general or specific applications is also possible in a variety of specifications.

EUMEPS has agreed on a set of standard product types in order to give transparency to the customers and to enable "fair" competition between EPS producers.

This is hence for EPS brought on the market without intended specific application or for internal use in "down-stream" products (e.g. sandwich panels); these are often called "commodity EPS products".

Table 16: EUMEPS EPS types without intended specific application ("commodity").

EUMEPS-TYPE	Compressive stress 10%	Bending strength	Thermal conductivity	Dimensional stability under normal laboratory conditions	Dimensional tolerances
EPS 60	60	100	$\leq 0,038$	$\leq 0.5$	L1,W1,T1,S1,P2
EPS 100	100	150	$\leq 0,036$	$\leq 0.5$	L1,W1,T1,S1,P2
EPS 150	150	200	$\leq 0,035$	$\leq 0.5$	L1,W1,T1,S1,P2
EPS 200	200	250	$\leq 0,034$	$\leq 0.5$	L1,W1,T1,S1,P2
EPS 250	250	300	$\leq 0,034$	$\leq 0.5$	L1,W1,T1,S1,P2
	CS(10), [kPa]	BS, [kPa]	Lambda,[W/mK]	DS(N), %	Table 1, classes

































All EPS types are available with or without of flame retardants. Products containing a flame retardant will achieve Euro class E (or better) and are identified with the addition of a red stripe. For historical reasons different member states the references in literature may differ and may continue to be used. For example reaction to fire class E may also be identified by the following equivalent definitions:



A or FRA United Kingdom  
 A1 Belgium  
 B1 Germany  
 F Sweden  
 M1 France, Spain  
 S Finland  
 SE Netherlands, Germany

For the EUMEPS types the following colour codes have been agreed for identification purposes:

*Table 17: EUMEPS colour coding for EPS types.*

EPS Eurotypes	Colour code for non flame retarded products		Colour code for flame retarded products	
	Description	Colour	Description	Colour
EPS 30	Brown		Brown + red	
EPS 50	Blue		Blue + red	
EPS 60	Blue + blue		Blue + blue + red	
EPS 70	Brown + brown		Brown + brown + red	
EPS 80	Orange		Orange + red	
EPS 90	Orange + orange		Orange + orange + red	
EPS 100	black		Black + red	
EPS 120	Green + green		Green + green + red	
EPS 150	yellow		Yellow + red	
EPS 200	Black + black		Black + black + red	
EPS 250	Violet		Violet + red	
EPS 300	Violet + violet		Violet + violet + red	
EPS 350	Grey		Grey + red	
EPS 400	Grey + grey		Grey + grey + red	
EPS 500	Black + green		Black + green + red	
EPS T	Green		Green + red	

The colour code is applied on at least one edge of the boards.

#### **5.4.2 Application**

In this document a overview of possible product/application combinations is given to make it easier making a choice for customers (authorities, contractors, suppliers, architects and owners).

The overview is given in a simple matrix, whereas the applications are taken from ISO TR 9774. This covers probably 95% of all the known building insulation EPS applications. Bullet points give possible and most used applications/product types combinations; left from these the EPS properties are too low for a reliable application; right from the bullet points the quality may be too good in relation to the price.

Table 18: Overview of examples of applications and EPS product types

Application versus EPS type	EPS S	EPS 60-100	EPS 100-150	EPS 150-200	EPS 200-250	EPS 250-300	EPS T
<b>CELLARS</b>							
Internal insulation	●	●	—	—	—	—	—
External, protected	=	=	●	●	—	—	—
Perimeter insulation	=	=	● <sup>+</sup> )	● <sup>+</sup> )	● <sup>+</sup> )	—	—
<b>GROUND FLOORS</b>							
Slab- on- ground	=	●	●	●	●	—	—
Concrete floor element	=	●	●	—	—	—	—
On construction floor	=	●	●	—	—	—	●
Renovation el.	=	● <sup>1)</sup> )	●	—	—	—	—
<b>FLOORS</b>							
Ceilings/ loft insulation	=	●	—	—	—	—	—
Floating floors	=	●	●	●	—	—	●
<b>WALLS/GABLES</b>							
Doublage	●	—	—	—	—	—	●
SIPS / others	=	●	●	—	—	—	—
Cavity wall insulation	●	● <sup>+</sup> )	●	—	—	—	—
Sandwich panels-steel	=	●	●	—	—	—	—
External insulation	●	●	—	—	—	—	●
ETICS	=	● <sup>+</sup> )	●	—	—	—	—
<b>PITCHED ROOFS</b>							
Internal-insulation (all)	=	●	—	—	—	—	—
Sandwich panels (all)	=	●	—	—	—	—	—
External insulation	=	●	● <sup>2)</sup> )	● <sup>2)</sup> )	—	—	—
<b>FLAT ROOFS</b>							
Warm roofs	=	● <sup>1)</sup> )	●	●	●	—	—
Cold roofs	=	●	●	—	—	—	—
Inverted roofs	=	=	=	●	—	—	—
<b>CIVIL ENG APPL.</b>							
All/ general	=	●	●	●	●	●	—

**LEGEND:**

● normally used in the EUMEPS member states.

= not possible from functional requirements.

— not necessary / applied normally unless properties are explicitly needed.

<sup>1)</sup> when load distribution boards are applied.<sup>2)</sup> when load bearing.

Depending on the “local” building regulations the properties required may be more severe (indicated: <sup>+</sup>) than given in EN 13163.

## 6 Voluntary quality marks

### 6.1 European marks

#### KEYMARK

The European quality mark KEYMARK can be used for all products, for which European standards or approvals exist and a scheme has been approved. Complete rules for thermal insulation products – one of the first family of construction products to have a KEYMARK scheme – have been created successfully. In Europe, the KEYMARK offers for thermal insulation material a common system of inspection, surveillance and certification. The KEYMARK will only be used in connection with an existing national quality mark (e. g. RAL quality mark in Germany).

Only bodies, which are already accredited as a European certification body for insulation material standards, are admitted to grant the KEYMARK.

To obtain the KEYMARK the manufacturer needs a complete product certification. This means he has to operate a factory production control and as well as continuous product surveillance by a third party.

The rules of the KEYMARK for thermal insulation materials assure, that the manufacturers in Europe are all subjected to the same criteria and procedures. This prevents unfair competition by different expensive quality systems operating to different monitoring systems. The KEYMARK is likely to be attractive to companies operating internationally. The KEYMARK will only be awarded in conjunction with an existing national quality mark, which will increase its visibility and enhance its international reputation. In this way, the manufacturer has the opportunity to label products, which are distributed in different countries, in the same way.

The complete product certification will create a high confidence with the customer. The manufacturer can demonstrate that the products comply with European specifications. Regarding which the new warranty law which inverts the burden of evidence in the first six month this offers more security for the manufacturer because he can prove, that his products comply with his claims and have been controlled by an independent body.

Some European countries have given a benefit to those thermal insulation products subjected to third party control by imposing no addition to the design value of thermal conductivity or additional fees for product assurance. It is already known from France (18 %) and Germany (15 %) that these countries will implement an addition on thermal conductivity for non third party controlled products and it can be foreseen that other countries may follow this system.

In addition Germany requires a conformity mark (Ü mark) for the confirmation of the application related requirements (DIN 4108-10) by a certification body, which also includes a continuous surveillance by a third party. The combination of the national quality mark and the KEYMARK will cover in future all required assessments on a national and a European basis. All required performances will be tested by only one testing body leading to savings for international companies.

The national quality marks won't be replaced by KEYMARK, but they must be based on European product standards in future. Therefore, the product needs to be tested only once to fulfil the requirements for both quality marks.

While the KEYMARK will assess the conformity of EPS with EN 13163, the national signs may focus in future on the conformity with the national application related requirements.

## **6.2 Voluntary national marks**

### **6.2.1 Austria GPH**

### **6.2.2 Belgium**

### **6.2.3 Czech Republic**

### **6.2.4 Denmark VIK**

### **6.2.5 Finland VTT**

### **6.2.6 France ACERMI**

### **6.2.7 Germany GSH and IVH-BFA**

Next to that, DIN V 4108-10 contains application related requirements for thermal insulation materials e. g. as for EPS in table 4.

DIN V 4108-4 contains regulations how to obtain the design value of the thermal conductivity to use for energy saving calculations such as EN 832. The design value,  $\lambda_U$ , will be calculated from the declared value of the thermal conductivity,  $\lambda_D$ , by the following equation:

$$\lambda_U = \gamma \cdot \lambda_D$$

The factor,  $\gamma$ , depends on the fact whether an optional approval from DIBt requiring a third party certification is involved or not. In cases where a notified body controls the FPC and the product properties the factor will be 1,05. In all other cases the factor is 1,2.

### **6.2.8 Greece**

### **6.2.9 Iceland**

### **6.2.10 Ireland**

### **6.2.11 Italy**

### **6.2.12 Luxemburg**

### **6.2.13 Malta**

### **6.2.14 Netherlands KOMO**

The current situation in the Netherlands is one, totally on a voluntary basis, that exists already for several decades in its present format. This set-up was the result of negotiation between authorities (the Ministries of Housing, Economic Affairs and Internal Affairs), building industry (suppliers, contractors, subcontractors), consultants (engineers and architects) and the certification bodies.

Three types of markings exist:

a product certificate, for products of which a product standard exists;

a technical approval with certification, for products or construction parts with its intended use/performance requirements;

a process-certificate for the application of specific products or kits based either on product standards or/and on performance requirements and application requirements.

All the types are bearing the KOMO label, third party control is carried out by accredited certification bodies as KIWA, Intron, IKOBKB and SKH.

In the building regulations ("Woningwet" and "Bouwbesluit") these labels are mentioned as labels for which is expected that the products/kits/processes fulfil at least the official requirements. They are all put on a list, which is yearly updated.

For the co-ordination of activities between certification bodies, authorities and the industry - including UEAtc and EOTA contacts - the "Stichting Bouwkwaliiteit (SBK)" - foundation for building quality, was formed in 1990. This foundation issues the permission to use the KOMO-label for marking to certification bodies.

At this moment the expectation is, that next to this quality labels (KOMO) the CE label as conformity label will be introduced as an extra. The EC is focussing on this KOMO system at this moment supposing it being a not-acceptable system next to the CE-marking and labelling.

#### **6.2.15 Norway**

#### **6.2.16 Portugal**

#### **6.2.17 Spain**

Based on UNE-EN-13163 and UNE-EN-13172, on a voluntary base, it is just a product certification. In the Building Regulations the standards are mentioned as reference but not the certification. For EPS, the N mark means CE marking with AoC system 1 for all specifications.

#### **6.2.18 Sweden**

#### **6.2.19 Switzerland**

#### **6.2.20 United Kingdom BBA**

In the UK the BSI Keymark has been used in the insulation sector but not specifically by the EPS industry. EPS manufacturers have relied on British Board of Agrément (BBA) or equivalent certification which covers not only the product quality but also the specific details of application. The more widely known applications for EPS are covered by this certification. In addition all producers of EPS have third party surveillance on their factory production control to BS EN ISO 9002.

## 7 References and bibliography

1. DIN 4102, Brandverhalten von Baustoffen.
2. Hamann, Klodt, Gellert, Pelzers. Long term behaviour of polystyrene foam classified as B1 respectively B2 material according to DIN 4102. Bauphysik 21 (1999), Journal 1. Ernst & Sohn Verlag, Berlin.
3. Gausepohl und R. Gellert. Kunststoff-Handbuch; 4. Hanser Verlag 1996.
4. Ojanen, T. & Kokko, E. Moisture Performance Analysis of EPS Frost Insulation. Insulation Materials: Testing and Applications: Third Volume, ASTM STP 1320, pp. 442-455, 1997.
5. Directive relating to Construction Products, Council Directive of 21 December 1988 (89/106/EEC)
6. EN 832: 1998 – Thermal performance of buildings – Calculation of energy use for heating – Residential buildings
7. EN 14309:2009, Thermal insulating products for building equipment and industrial installations – Factory made products of expanded polystyrene (EPS) – Specification
8. EN 13168: 2008, Thermal insulation for buildings – Factory made wood wool (WW) products – Specification
9. EN ISO 9229: Thermal insulation – Definition of terms
10. EN 45020:2007, Standardization and related activities - General vocabulary
11. EN ISO 13943, Fire safety – Vocabulary
12. EN 12114: 2000, Thermal performance of buildings – Air permeability of building components and building elements
13. EN 13009: 2000, Hygrothermal performance of building materials and products – Determination of hygric expansion coefficient
14. EN 12570: 2000, Hygrothermal of building materials and products – Determination of moisture content by drying at elevated temperature
15. EN ISO 12571: 2000, Hygrothermal of building materials and products – Determination of hygroscopic sorption properties
16. EN 12524: 2000, Building materials and products – Hygrothermal properties- Tabulated design values
17. BS 6203: 1998, Guide to the fire characteristics and fire performance of expanded polystyrene materials (EPS and XPS) used in building applications
18. ISO DTR 9774, Properties of thermal insulation products for buildings according to their application – Guideline for the harmonization of international standards or specifications
19. Zehendner, Verhalten von Schaumkunststoffen unter Druckbeanspruchung bei 20 und 80°C
20. AGI-Arbeitsblatt Q 133 – Harte Schaumkunststoffe als Dämmstoffe für betriebstechnische Anlagen – Teil 1 Polystyrol(PS)-Partikelschaum
21. Zehendner, Untersuchungen der mechanischen Eigenschaften von Schaumkunststoffen im Bereich von –180 °C bis +70 °C
22. EN 12430: 1998, Thermal insulating products for building application – Determination of behaviour under point load
23. EN 13788, Hygrothermal performance of building components and building elements – Estimation of internal surface temperature to avoid critical surface humidity and calculation of interstitial condensation
24. EN 12354-2, Building acoustics – Estimation of acoustic performance of buildings from the performance of elements – Part 2: Impact sound insulation between rooms
25. EN 13950, Gypsum plasterboard thermal/acoustic insulation composite panels. Definitions, requirements and test methods
26. EN 14509 Self-supporting double skin metal faced insulating sandwich panels - Factory made products – Specification
27. SP 2687 Resistance to cyclic compressive loading with square-wave load
28. Lågtidsbelastning med extrapolering enligt EN 1606, EPS materail: Plastolit P-100. Swedish National Testing and Research Institute, Gothenburg, 2001
29. Guidance Paper H, A Harmonised approach Relating to Dangerous Substances Under the Construction Products Directive
30. DG Enterprise G5 [database of dangerous substances or components]. URL: <http://europa.eu.int/comm/enterprise/construction/internal/dangsub/dangalf.htm>
31. EN 27345, Thermal insulation – Physical quantities and definitions
32. EN ISO 1182, Reaction to fire tests for building products – Non-combustibility test

33. EN ISO 1716, Reaction to fire tests for building products – Determination of the heat of combustion
34. ISO 12491, Statistical methods for quality control of building materials and components
35. ISO 9251, Thermal insulation – Heat transfer conditions and properties of materials – Vocabulary
36. ISO 9288, Thermal insulation – Heat transfer by radiation – Physical quantities and definitions
37. ISO 9346, Thermal insulation – Mass transfer – Physical quantities and definitions
38. Swinton, Bomberg, Kumaran and Maref: In situ Performance of Expanded Molded Polystyrene in the Exterior Basement Insulation Systems (EIBS). Published in Journal of Thermal Env. & Bldg. SCI. Vol. 23-October 1999.
39. EN 13471 Thermal insulating products for building equipment and industrial installations – Determination of the coefficient of thermal expansion
40. DIN 53428, Prüfung von Schaumstoffen; Bestimmung des Verhaltens gegen Flüssigkeiten, Dämpfe, Gase und feste Stoffe, 1986-08
41. EN 13787, Thermal insulation products for building equipment and industrial installations – Determination of declared thermal conductivity
42. ISO/CD 12575 Building applications – Foundation insulating systems
43. European LCA-data for EPS building products, Seijdel R. R., PRC-Bouwcentrum report 886.001, August 1998
44. Critical review on LCA-data for EPS, Schuurmans A., Intron report M715490, 13 October 1998
45. ISO 14040 Environmental management - Life cycle assessment - Principles and framework
46. Erkennbare und verlässliche Qualität – europaweit, Güteschutzgemeinschaft Hartschaum e. V., Celle
47. VTT Building technology, Research Report No. RTE10018/96, Moisture-physical function of EPS frost-insulating materials in building foundations, Erkki Kokko, Tuomo Ojanen, Seppo Saarelainen, Harri Kivikoski, Espoo, Finland, 1996
48. ASTM D 1929 Standard Test Method for Determining Ignition Temperature of Plastics
49. Einfluß des Feuchtegehaltes auf die Wärmeleitfähigkeit von Bau- und Dämmstoffen, Bau- und Wohnforschung 1988
50. Struik, L.C.E., Physical aging in amorphous polymers and other materials, Elsevier Scientific Publishing Company, 1978
51. Agreement on technical cooperation between ISO and CEN (Vienna agreement)
52. CEN TR 15985 Voluntary certification of the raw material
53. FIW München: Achtziger, J.: Polystyrol- Hartschaum als Dämmstoff im Hochbau – 25 Jahre Forschung im Dienst der Qualitätssicherung, Veröffentlichung der Güteschutzgemeinschaft Hartschaum GSH (1987)
54. EPS- Verband Schweiz, Küssnacht: Langzeitverhalten von EPS- Dämmstoffen, aus: Alterungsbeständigkeit von EPS mit Langzeitnachweis, Carbotech AG, Basel, S-E-E.CH Tool (2004)
55. Construction Products Regulation No. 305/2011 of 09/03/2011
56. CROW Richtlijn, Lichte ophoogmaterialen, 2013
57. TMC/Afloat, Rekenmethode voor de toepassing van EPS in de GWW, 25/01/2013

## 8 Authors

This document is revised by the experts of the EUMEPS TWG TG White Book

Dolf van Moorsel (Chairman)  
Tapio Kilpeläinen (until 2010)  
Edmar Meuwissen  
Lutgarde Neirinckx  
Hans Tepper  
David Thompsett  
Klaus Zipp



## 9 Alphabetic register

### A

acoustic performance.....	47
Affiliated CEN members .....	75
Annex ZA .....	5
<i>applications</i> .....	64

### B

Background .....	5
barriers to trade .....	5
bending strength .....	9
building foundations .....	43
Burning droplets.....	25

### C

Case of dispute .....	17
<i>Coefficients of thermal expansion</i> .....	52
<i>Colour coding</i> .....	63
composite systems .....	10
Compressive load .....	31
compressive stress .....	9
compressive stress at 10 %.....	5
confidence level .....	3, 10
CPD.....	5

### D

declared thermal conductivity .....	41
Design.....	3
design thermal conductivity .....	41
drained .....	43
Durability of compressive strength .....	27

### E

equivalent weighted normalized sound pressure level .....	47
Essential Requirements .....	6
ETICS.....	10
EUMEPS.....	63
Euroclasses .....	26
European Calculation standards.....	59
Eurotypes .....	63

### F

factory production control .....	1
FIGRA.....	25
Fire Growth Rate Index .....	25
flame retardants.....	62
Flaming droplets/ particles.....	24
flanking elements .....	48

floating floor .....	47
foundations.....	43
fractile .....	3
freeze thaw resistance .....	43
frost insulation .....	44

### G

Grouping .....	5
GSH .....	8

### H

heat release .....	26
Hygiene and environment.....	6

### I

ignitibility .....	2
indirect test .....	14
indirect testing .....	7
interpretative documents .....	6

### K

k factors .....	3
-----------------	---

### L

Lateral Flame Spread .....	25
Length .....	23
LFS .....	25

### M

Mechanical resistance and stability .....	6
migration.....	26
moisture conversion factor .....	41

### N

National Application rules.....	60
national standardisation .....	7

### O

outlier.....	13
--------------	----

---

**P**

permeability .....	45
practical long term water content.....	43
predicted values .....	11
prediction interval .....	10
Protection against noise.....	6

---

**R**

Reaction to fire.....	6, 9
-----------------------	------

---

**S**

Safety in case of fire .....	6
Safety in use .....	6
sampling .....	11
SCC .....	6
scope .....	5
screed .....	47
SMOGRA.....	25
Smoke production .....	24, 25
Standardisation .....	6

Standing Committee for Construction .....	6
---	---

---

**T**

testing frequencies.....	13
testing machine.....	2
thermal conductivity .....	13, 5, 6, 7
Thermal conductivity .....	1
THR <sub>600</sub> .....	25
Total Heat Release .....	25
Traceability.....	16

---

**V**

variance of the density.....	12
------------------------------	----

---

**W**

water vapour permeability .....	45
weighted normalized impact sound pressure level .....	48
weighted reduction of impact sound pressure level.....	47
weighted standardized impact sound pressure level.....	48

## 10 Annex A Tables

Table A.1 List of symbols, explanations and units

Symbol	Explanation	Unit
$1 - \alpha$	confidence level	1
$\alpha_{th}$	coefficient of thermal expansion	1/K
$c_p$	specific heat capacity	J/(kg·K)
$\vartheta$	temperature	°C
$d_{meas}$	measured thickness	m
$D$	water vapour diffusion coefficient	m <sup>2</sup> /h
$\delta$	water vapour permeability	mg/(Pa·h·m)
$\delta_{air}$	water vapour permeability of the air	mg/(Pa·h·m)
$\vartheta_{mean}$	mean temperature	°C
<i>FIGRA</i>	Fire growth rate index	W/s
$F_w$	moisture conversion factor	1
$F_s$	Flame spread	mm
$\gamma$	factor to calculate $\lambda_U$ (German regulations)	1
$k_{n,p,1-\alpha}$	$k$ factor	1
$\lambda_g$	thermal conductivity at a mean temperature $\vartheta$	W/m·K
$\lambda_{lim}$	limit value of thermal conductivity	W/m·K
$\lambda_D$	declared thermal conductivity	W/m·K
$\lambda_{meas}$	measured thermal conductivity	W/m·K
$\lambda_U$	design thermal conductivity	W/m·K
$\lambda_u$	design thermal conductivity in relationship to the moisture content $u$	W/m·K
$L_{n,w,eq}$	equivalent weighted normalised sound pressure level	dB
$L'_{n,w}$	weighted normalised impact sound pressure level	dB
$\Delta L_w$	weighted reduction of impact sound pressure level	dB
$L'_{nT,w}$	weighted standardized impact sound pressure level	dB
<i>LFS</i>	lateral flame spread	m
$m$	mass	kg
$\Delta m$	mass difference	kg
$m'$	mass per unit area	kg/m <sup>3</sup>
$m'_0$	mass per unit area	kg/m <sup>3</sup>
$\mu$	water vapour diffusion resistance factor	1
$n$	number of measurements	1
$p$	fractile	1
<i>PCS</i>	gross calorific potential (pouvoir calorifique superieur)	MJ/kg
$q$	ratio	1
$Q$	energy	J
$R_D$	declared thermal resistance	m <sup>2</sup> K/W
$R_{meas}$	measured thermal resistance	m <sup>2</sup> K/W
$\sigma_c$	alternative stress (according EN 1606)	kPa
$s1 - s3$	Additional reaction to fire classes	non
$d0 - d2$	Additional reaction to fire classes	non
$t_f$	flaming time	s
$\Delta T$	temperature difference	K
<i>THR</i> <sub>600</sub>	Total Heat Release during the first 600 seconds	MJ
<i>TSP</i> <sub>600s</sub>	Total smoke production	m <sup>2</sup>
$u$	Moisture content	vol-%
$V$	volume	m <sup>3</sup>
$W_p$	practical water content	vol-%
$x_{th}$	dimension depending on temperature	m
$x$	dimension	m
$z$	fractile of the standardised normal distribution	1

The term  $1 - \alpha$  is described as prediction interval in EN 13163. In the context of its use in EN 13163 the correct term is confidence level.

Table A.2: Abbreviations

AoC	Attestation of conformity
ASTM	American Society for Testing and Materials (American standardisation body)
AVCP	Assessment and Verification of the Constancy of Performance
BR	Basic Requirement
CEA	Civil Engineering Application
CEN	European Committee for Standardisation (Comité Européen de Normalisation)
CPD	Construction Products Directive
CPR	Construction Products Regulation
CUAP	Common Unique Acceptance Procedure
DIBt	Deutsches Institut für Bautechnik (German Regulator Body)
DOA	Date of Acceptance
DoC	Declaration of Conformity
DoP	Declaration of Performance
DOW	Date of Withdrawal
EEA	European Economic Area
EC	European Commission
EN	European Norm (European Standard)
EoC	Evaluation of Conformity
ER	Essential Requirement
EOTA	European Organisation for Technical Approvals
EPS	Expanded Polystyrene
ETA	European Technical Approval
ETAG	European Technical Guideline
ETICS	External thermal insulation composite systems
EU	European Union
EUMEPS	European Manufacturers of EPS
FIGRA	Fire Growth Rate Index
FIW	Forschungsinstitut für Wärmeschutz e. V., München
FPC	Factory production control
FR	Flame retarded
ISO	International Standards Organization
ITT	InInitial Type testing
LFS	Lateral Flame Spread
MRA	Mutual Recognition Agreements
PECA	Protocol to the European Agreement on Conformity Assessment
prEN	provisional European Norm (European standard)
PTD	Product Type Determination
SBI	Single Burning Item
SCC	Standing Committee of Construction
SIPS	Structurally Insulated Panel Systems
SMOGRA	Index for rate of Smoke Development
SP	Swedish National Testing and Research Institute, Gothenburg
TC	Technical Committee
UAP	Unique Acceptance Procedure
UEAtc	Union Européenne pour l'Agrément Technique dans la Construction (European Union of Agrément)
VCP	Verification of the Constancy of Performance
VTT	Finish Technical Research Center
WG	Working Group
WI	Work Item

Table A.3: CEN Members and affiliated CEN members

<b>Abbreviation</b>	<b>Organisation</b>	<b>Country</b>
AENOR	Asociación Española de Normalización y Certificación	Spain
AFNOR	Association Française de Normalisation	France
ASI	Austrian Standards Institute	Austria
ASRO	Romanian Standards Association	Romania
BDS	Bulgarian Institute for Standardisation	Bulgaria
BSI	British Standards Institution	United Kingdom
CYS	Cyprus Organisation for Standardisation	Cyprus
DIN	Deutsches Institut für Normung e.V.	Germany
DS	Danish Standards	Denmark
ELOT	Hellenic Organization for Standardization	Greece
EVS	Estonian Centre for Standardisation	Estonia
HZN	Croatian Standards Institute	Croatia
ILNAS	Institut Luxembourgeois de la normalisation, de l'accréditation, de la sécurité et qualité des produits et services	Luxembourg
IPQ	Instituto Português da Qualidade	Portugal
IST	Icelandic Standards	Iceland
LST	Lithuanian Standards Board	Lithuania
LVS	Latvian Standards Ltd	Latvia
MSA	Malta Standards Authority	Malta
MSZT	Hungarian Standards Institution	Hungary
NBN	Bureau de Normalisation/Bureau voor Normalisatie	Belgium
NEN	Nederlands Normalisatie-instituut	Netherlands
NSAI	National Standards Authority of Ireland	Ireland
PKN	Polish Committee for Standardization	Poland
SFS	Suomen Standardisoimisliitto r.y.	Finland
SIS	Swedish Standards Institute	Sweden
SIST	Slovenian Institute for Standardization	Slovenia
SN	Standards Norway	Norway
SNV	Schweizerische Normen-Vereinigung	Switzerland
SUTN	Slovak Standards Institute	Slovakia
UNI	Ente Nazionale Italiano di Unificazione	Italy
UNMZ	Czech Office for Standards, Metrology and Testing	Czech Republic

Affiliated CEN members are not obliged to follow the CEN rules and to implement all harmonised standards issued by CEN. They can be involved in the creation but not in the voting process of European standards.